

Light-induced superconductivity via dynamical Hubbard U

Michael A. Sentef
lab.sentef.org

Funded through DFG Emmy Noether programme (SE 2558/2)

Bloch group meeting, MPQ Munich, January 19, 2021

Optical response of a superconductor

$$j(t) = \int_{-\infty}^{\infty} dt' \sigma(t - t') E(t')$$


$$\sigma_{\text{Drude}}(\omega) = \frac{ie^2(n/m)_{\text{eff}}}{\omega + i/\tau}$$

Dissipationless case: $1/\tau \rightarrow 0^+$

Real part: delta-function peak at zero frequency

Imaginary part: $1/\omega$ divergence


n = superfluid density

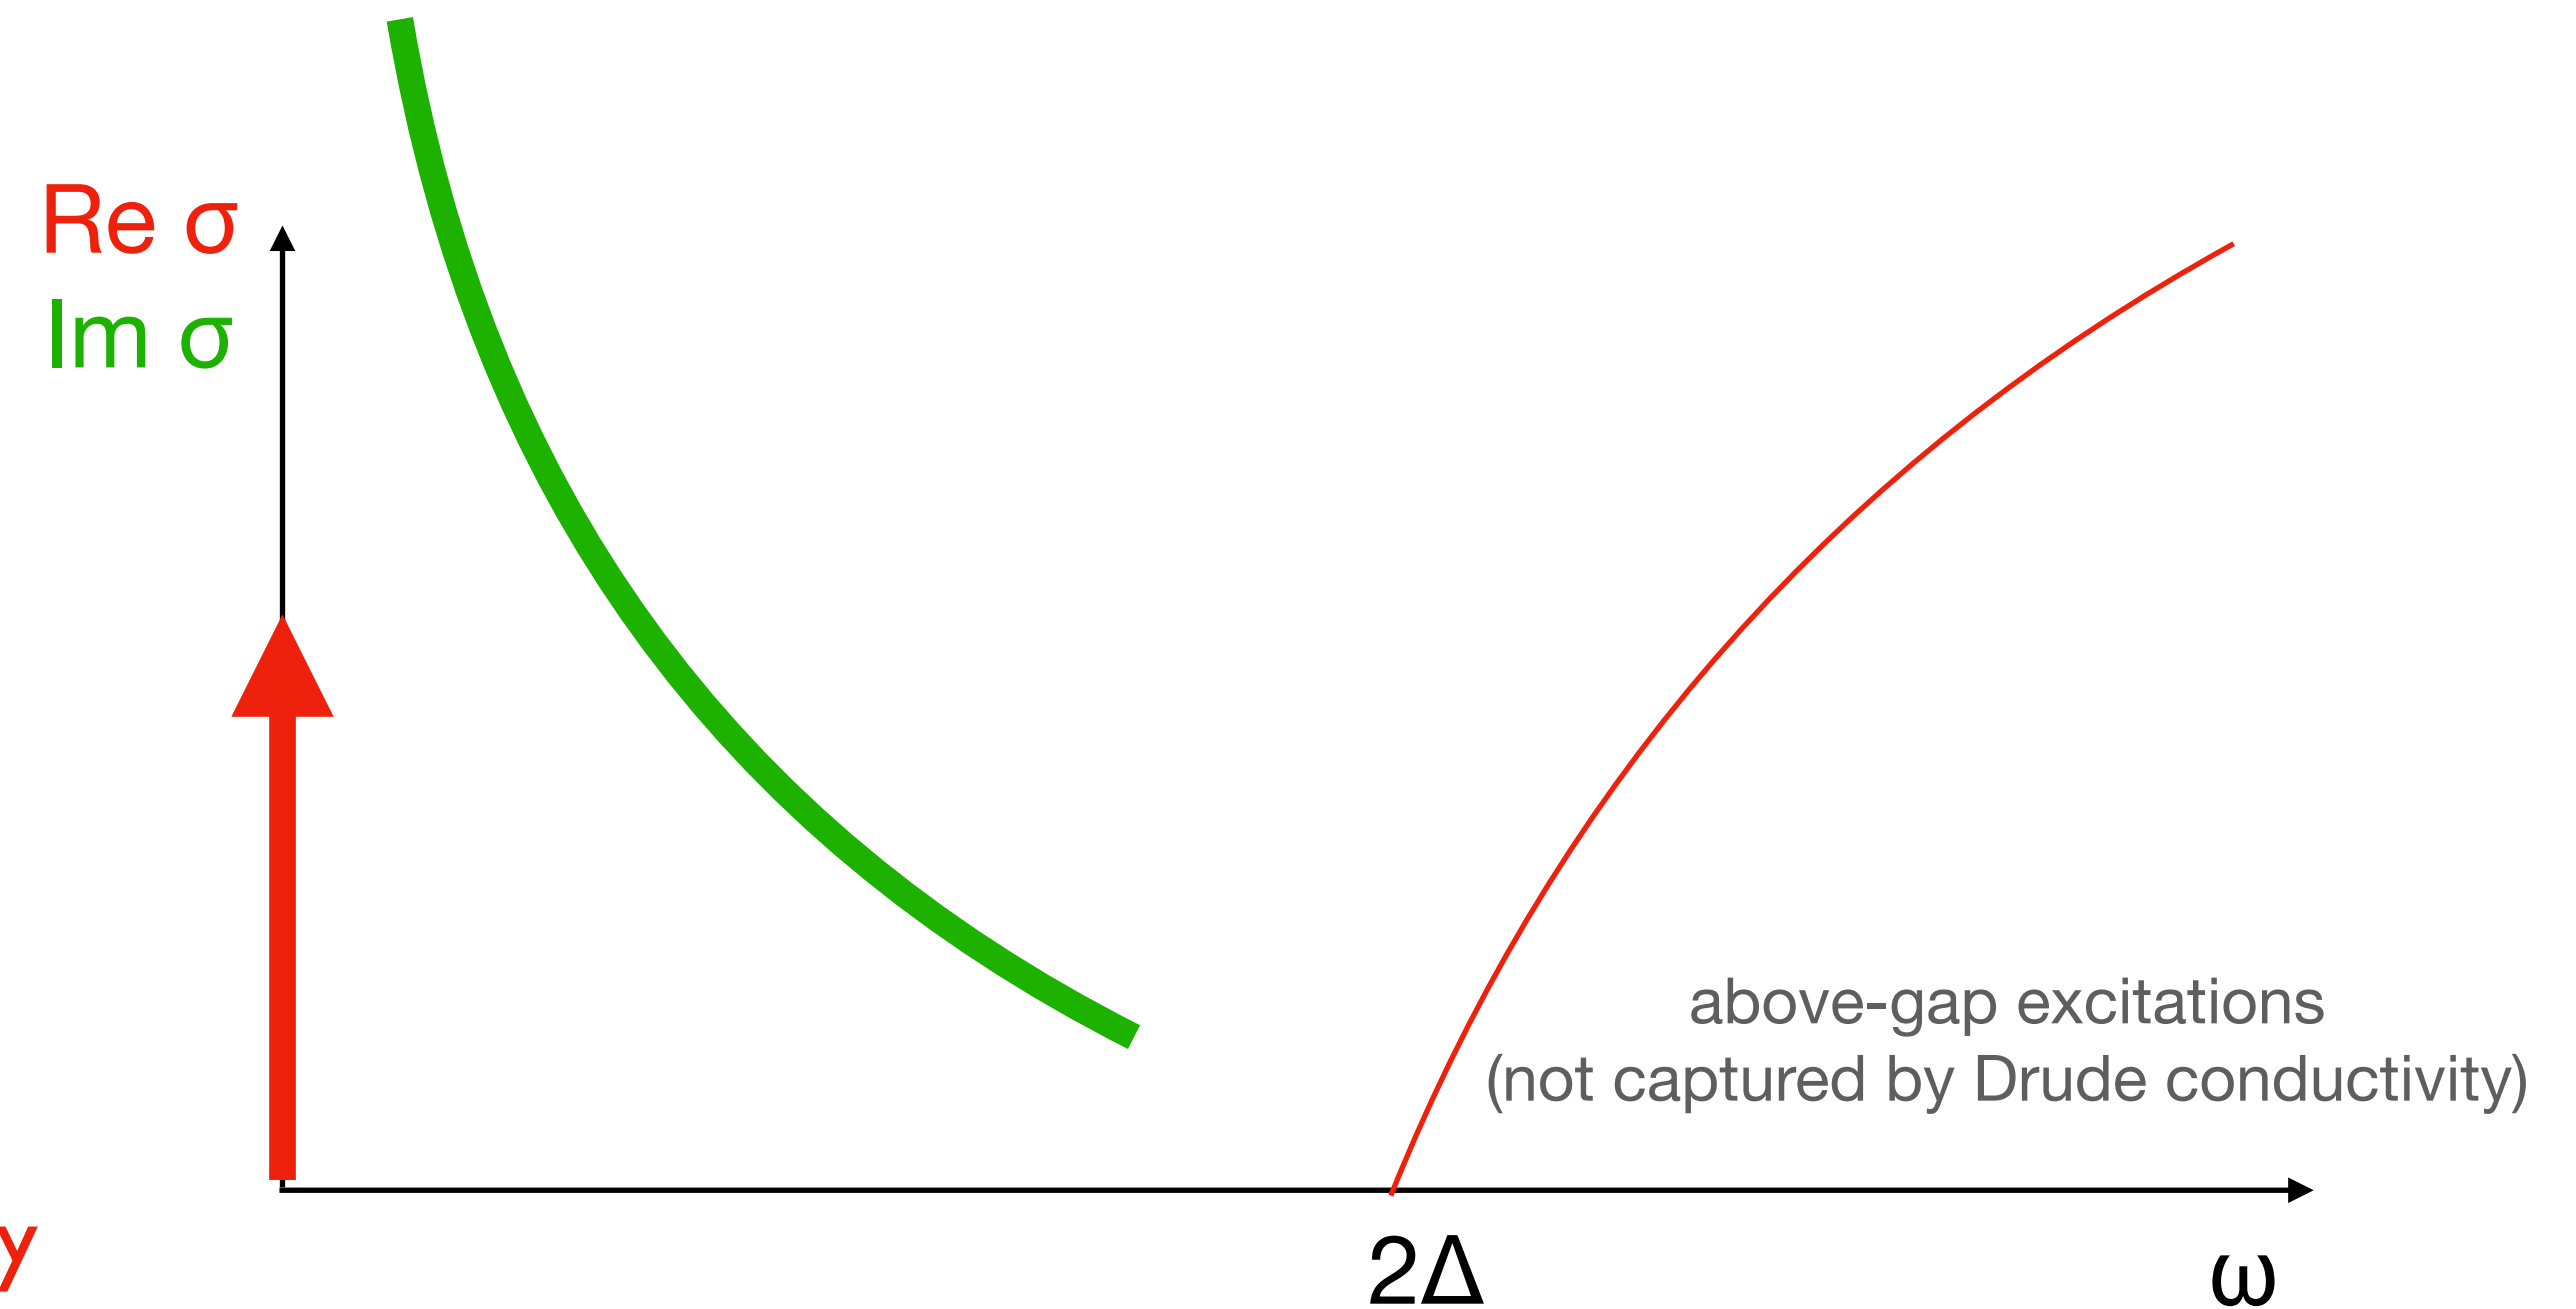


The weight of the delta-function peak / divergence in $\text{Re}/\text{Im } \sigma$ measures the superfluid density!

Light-induced superconductivity

Optically driven superconductivity via vibrational excitation

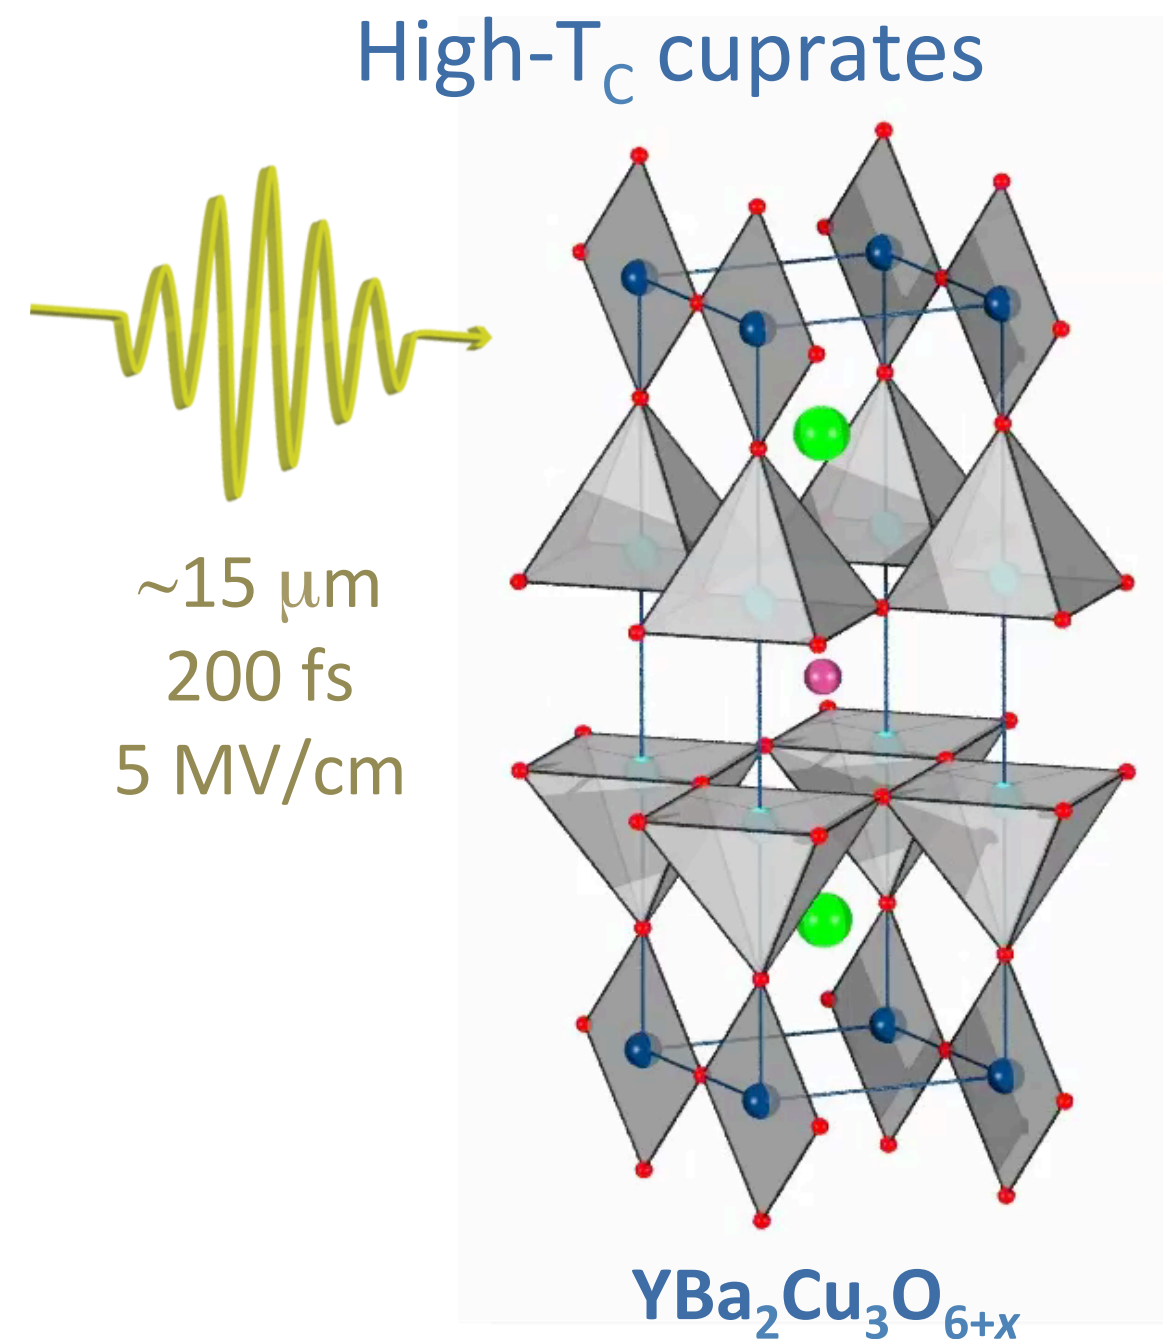

W. Hu *et al.*, Nat. Mater. **13**, 705 (2014)
R. Mankowsky *et al.*, Nature **516**, 71 (2014)

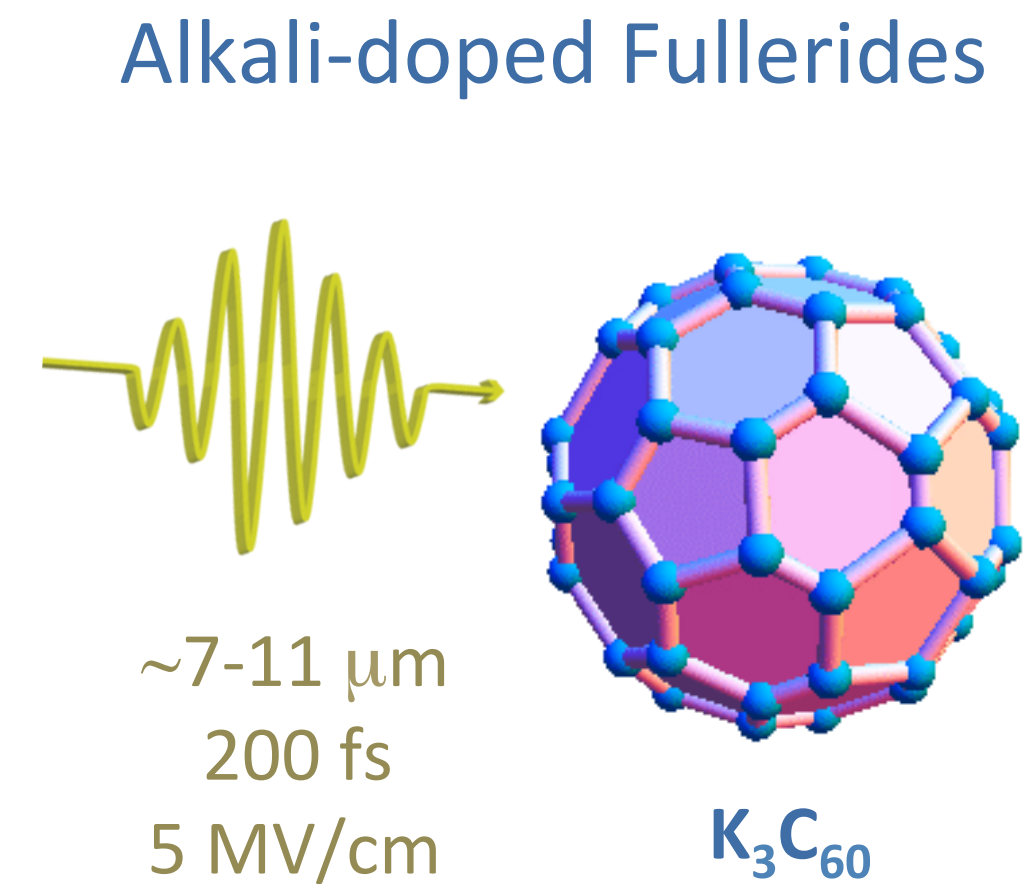


M. Mitrano *et al.*, Nature **530**, 461 (2016)
A. Cantaluppi *et al.*, Nat. Phys. **14**, 837 (2018)

Light-induced superconductivity

Driving the apical oxygen phonon in YBCO




~15 μm
200 fs
5 MV/cm

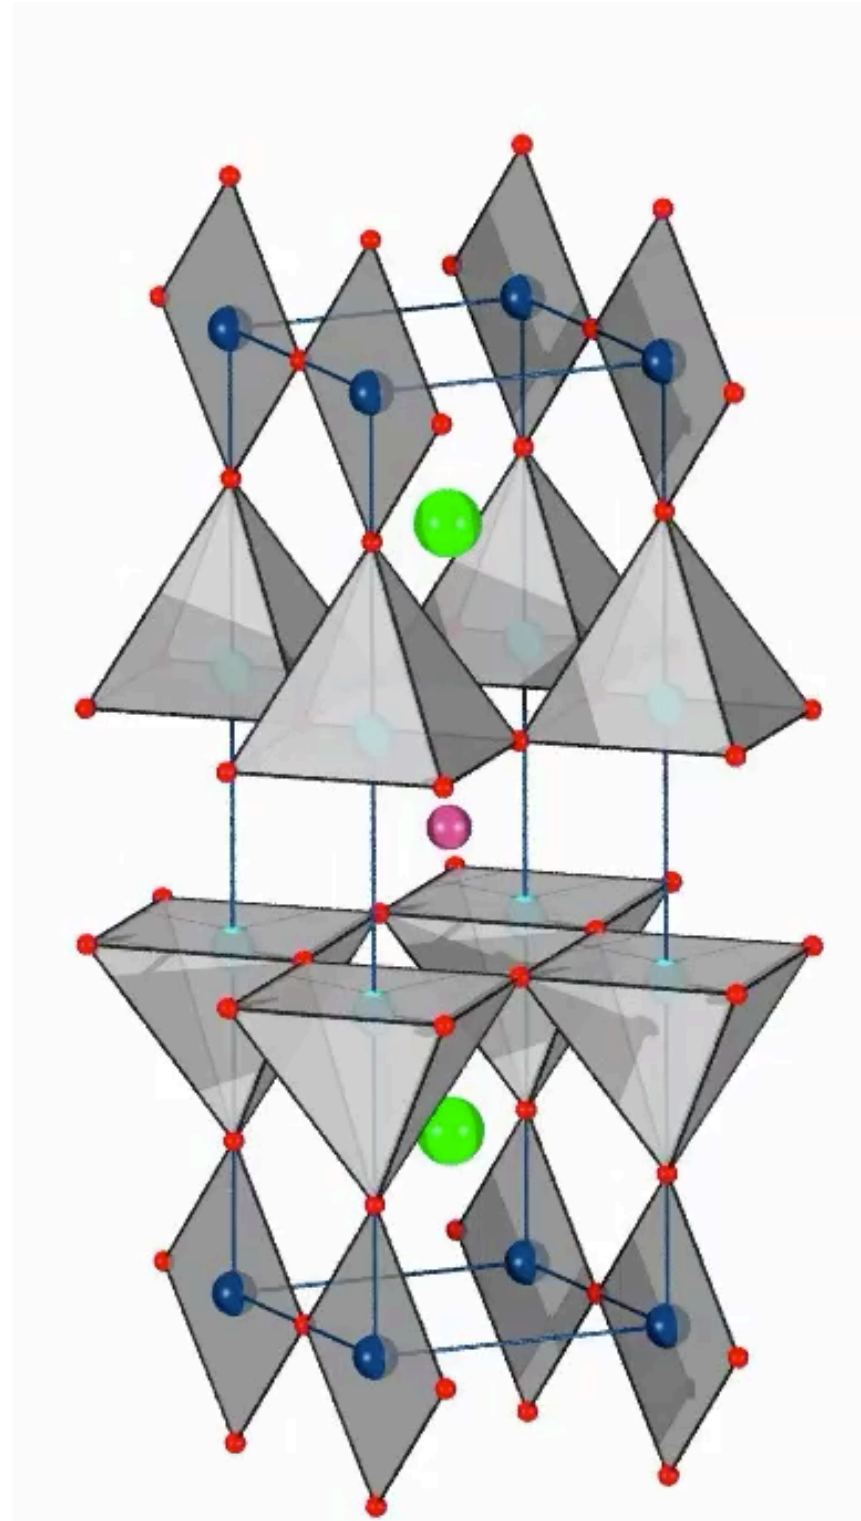


S. Kaiser *et al.*, Phys. Rev. B **89**, 184516 (2014)
C. Hunt *et al.*, Phys. Rev. B **94**, 224303 (2016)

1) Transient Plasma Resonance

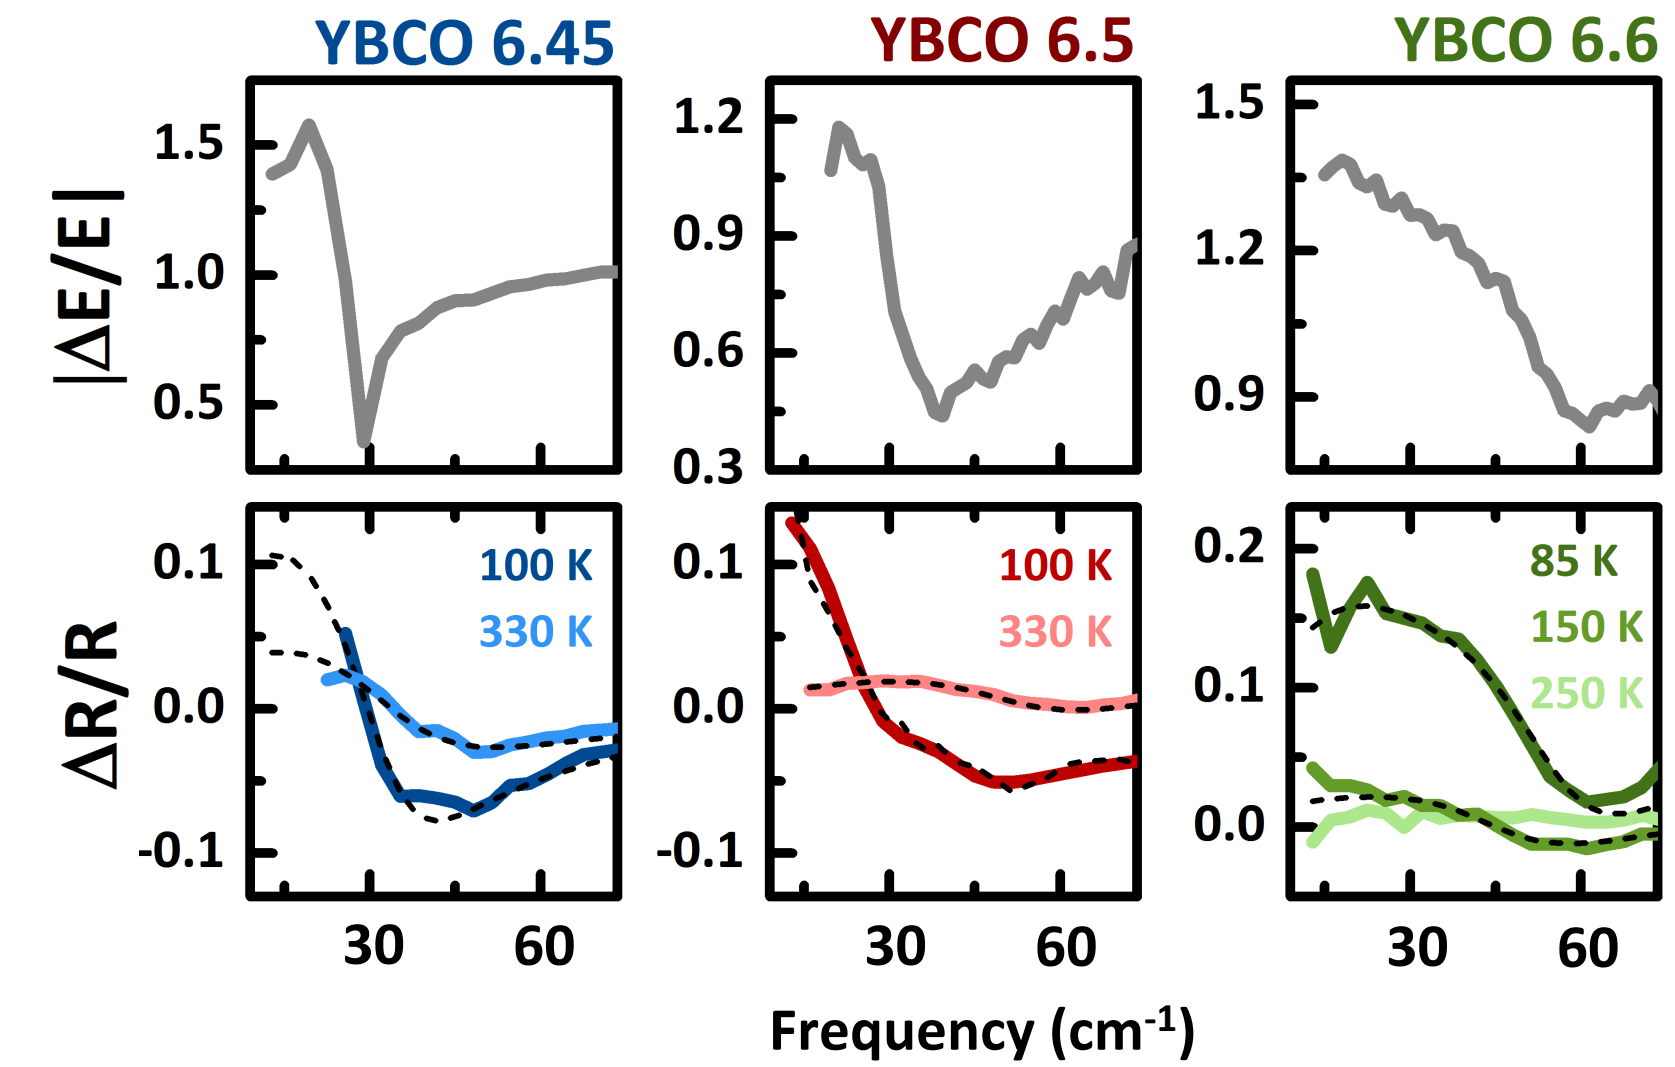


2) Divergent imaginary conductivity

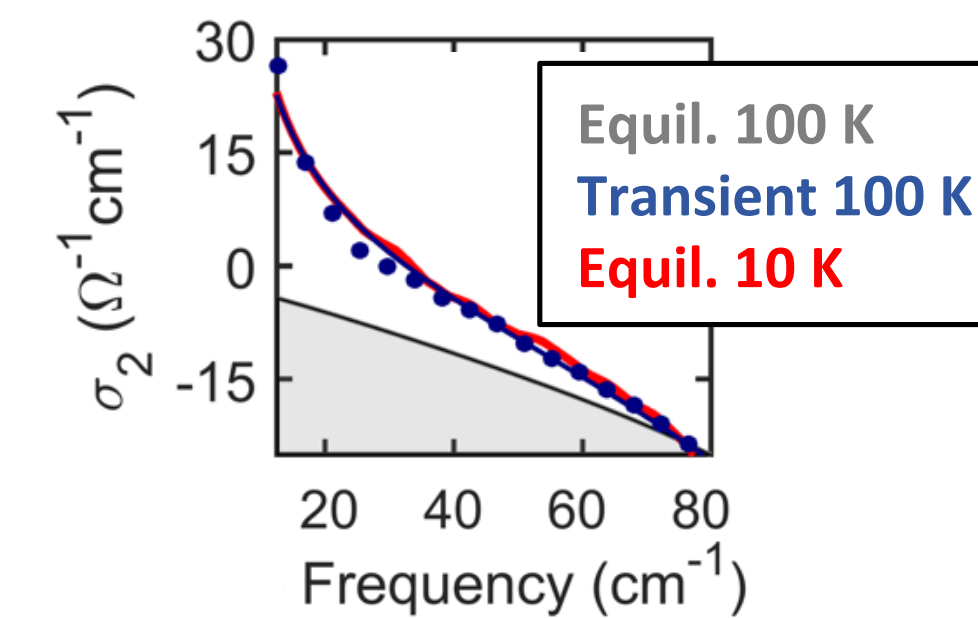


Light-induced superconductivity


Driving the apical oxygen phonon in YBCO

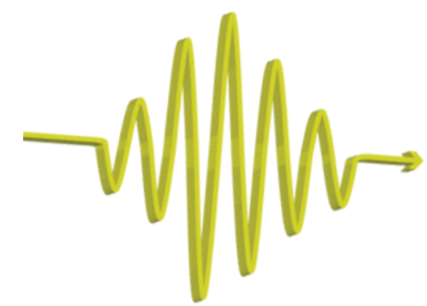

~15 μm
200 fs
5 MV/cm

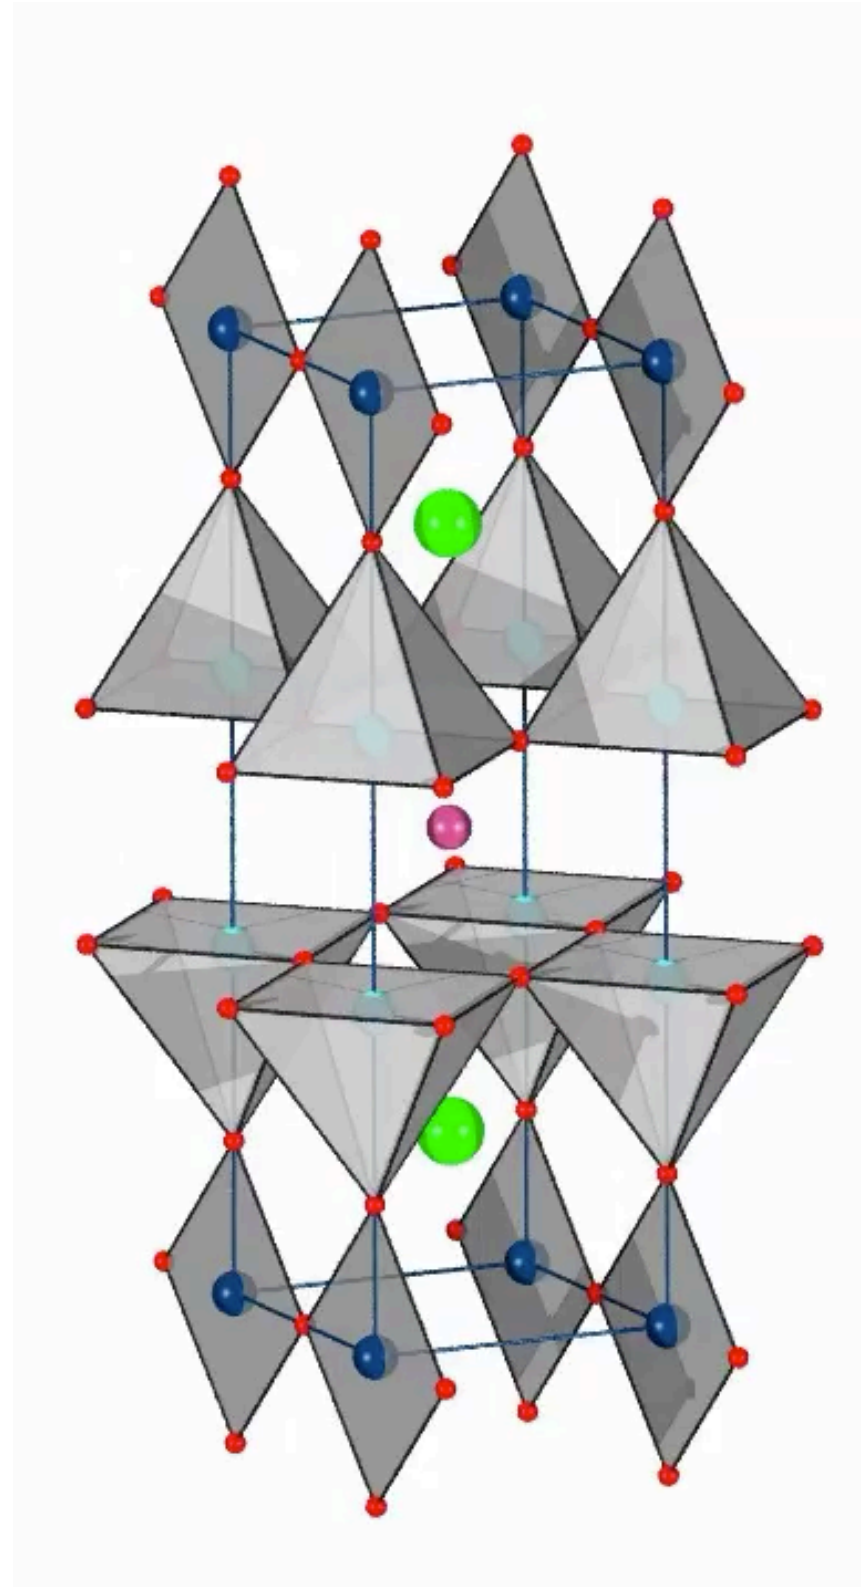




S. Kaiser *et al.*, Phys. Rev. B **89**, 184516 (2014)
C. Hunt *et al.*, Phys. Rev. B **94**, 224303 (2016)

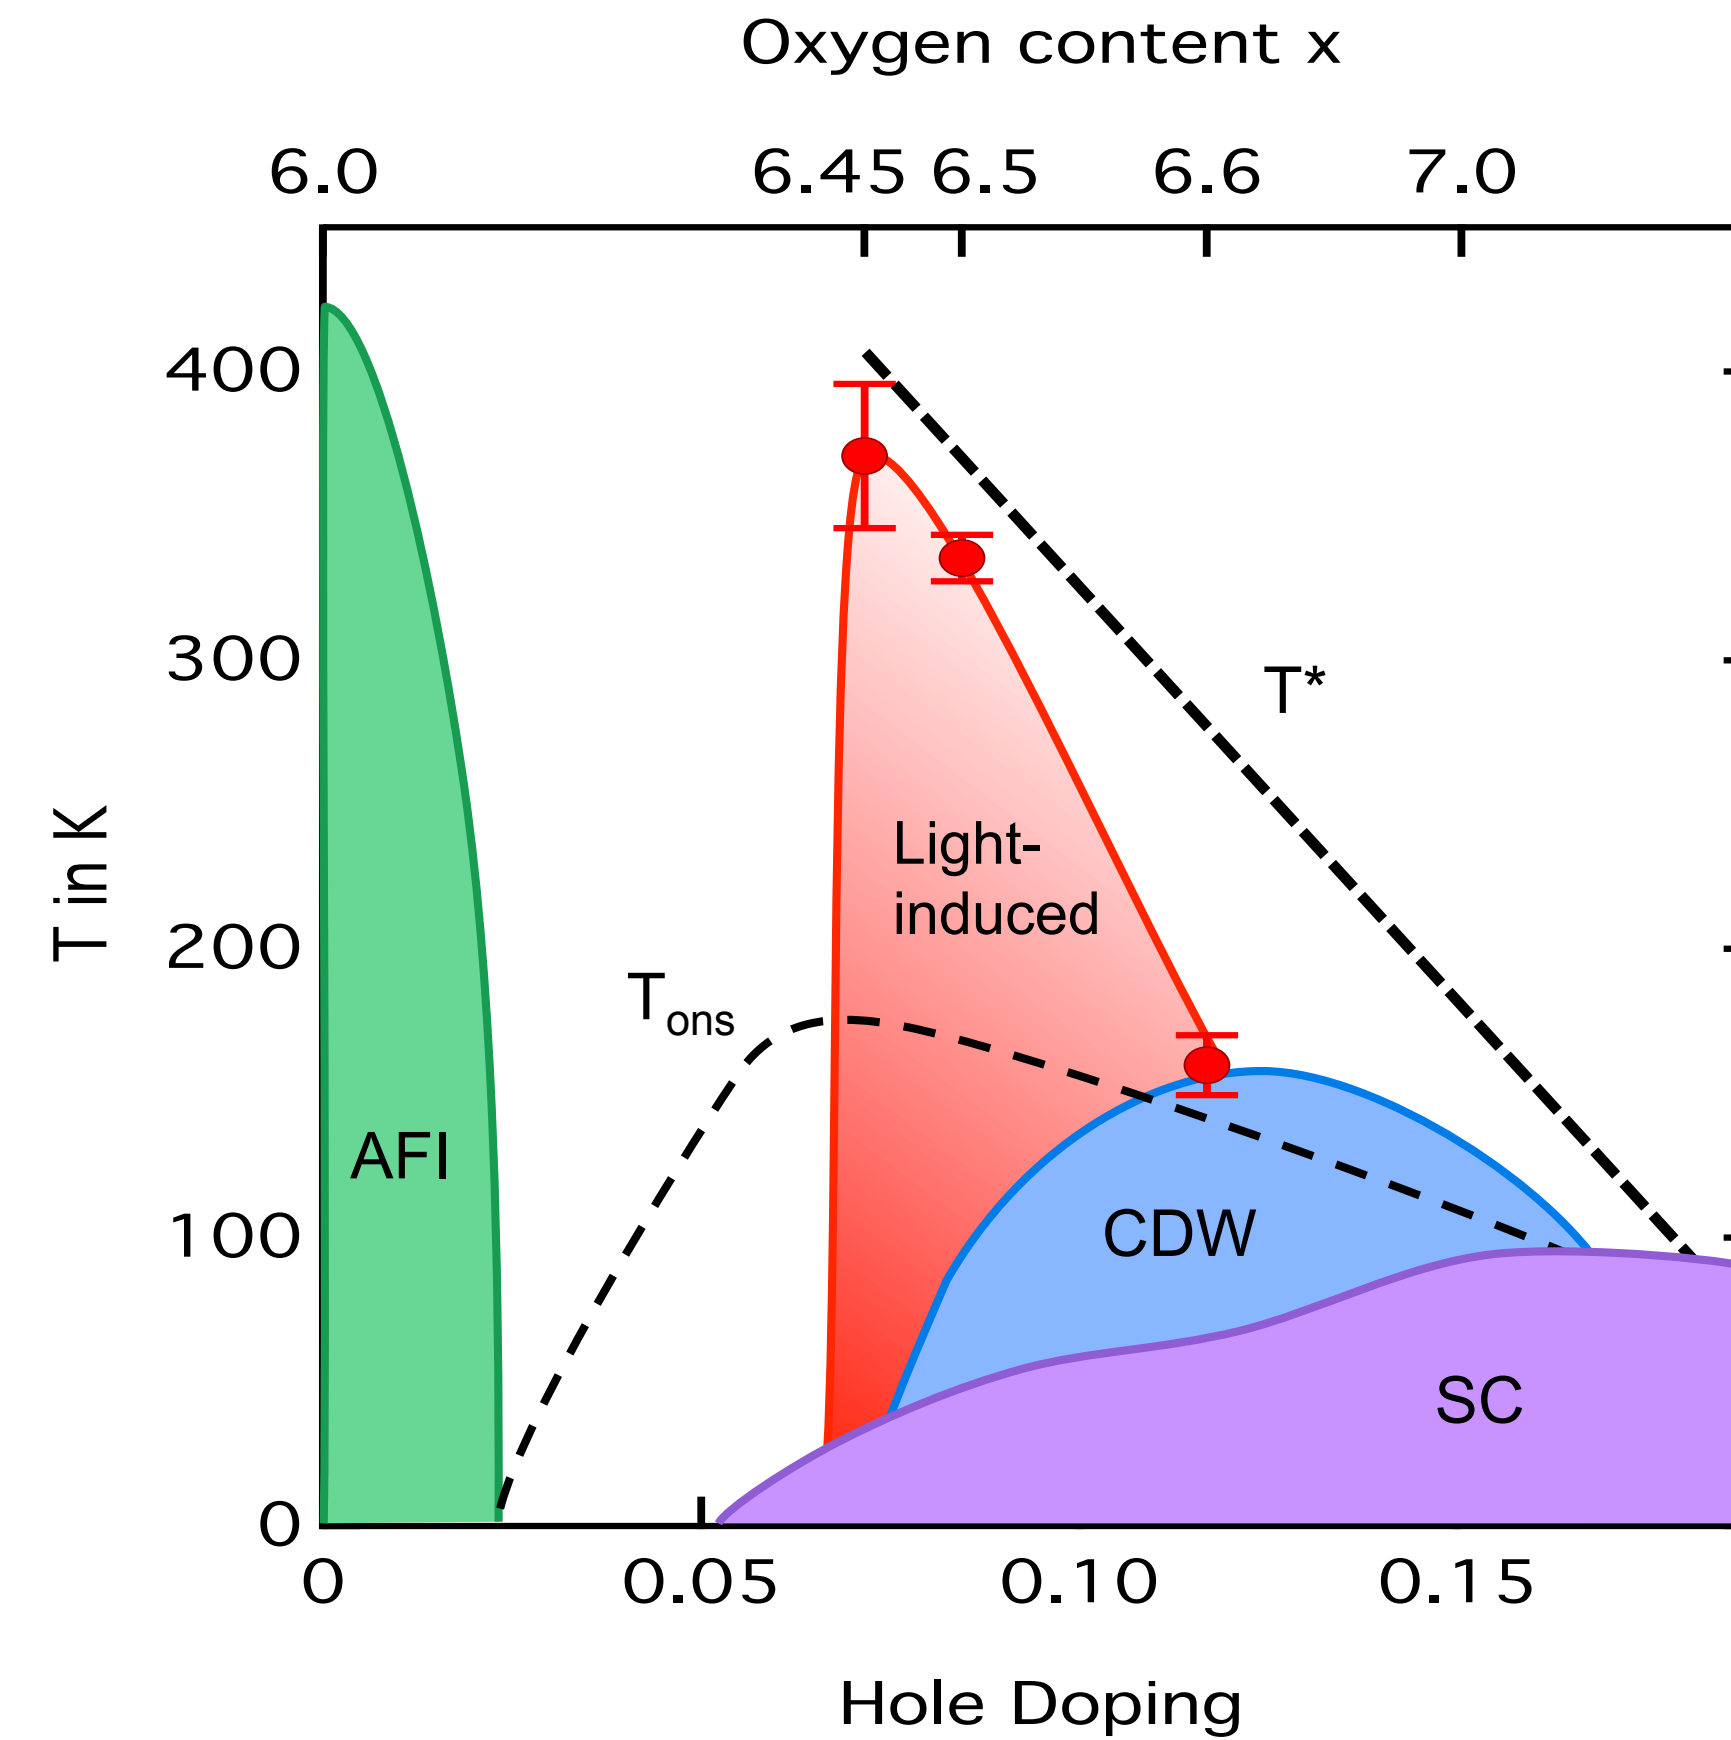

Light-induced superconductivity

Optically driven superconductivity in K_3C_{60}

K_3C_{60}
 $T_C = 20\text{ K}$

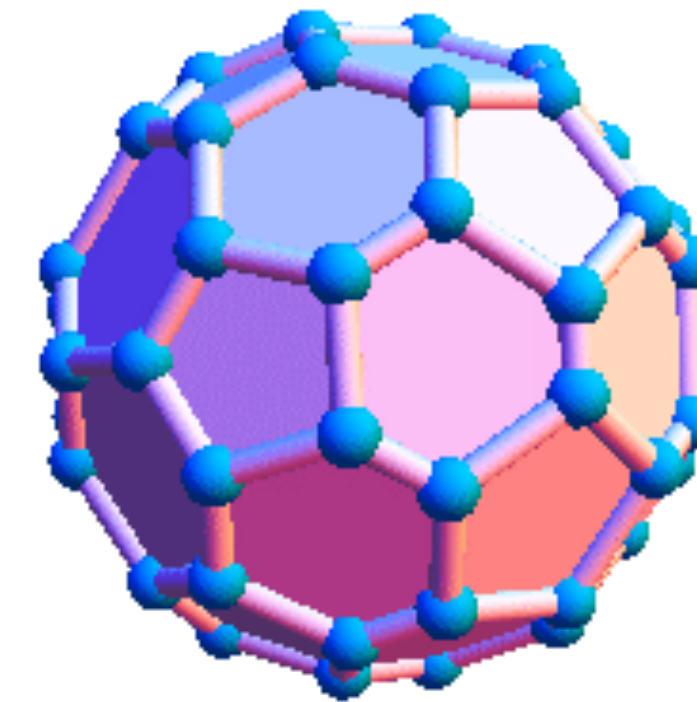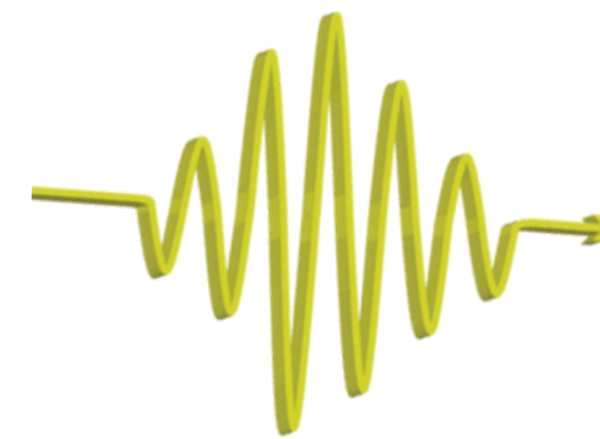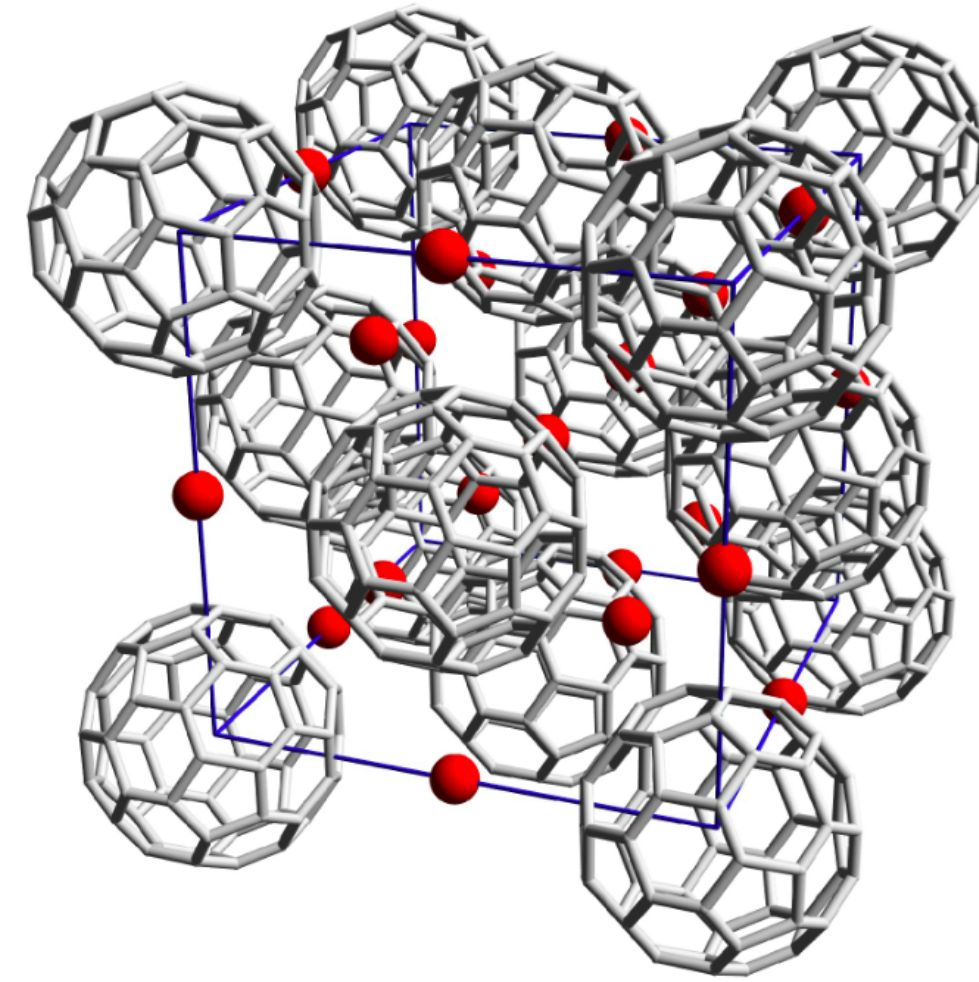


$\sim 7\text{-}11\ \mu\text{m}$
200 fs
5 MV/cm

M. Mitrano *et al.*, Nature **530**, 461 (2016)
A. Cantaluppi *et al.*, Nat. Phys. **14**, 837 (2018)


Light-induced superconductivity

Optically driven superconductivity in K_3C_{60}

Equilibrium
 $T < T_c$

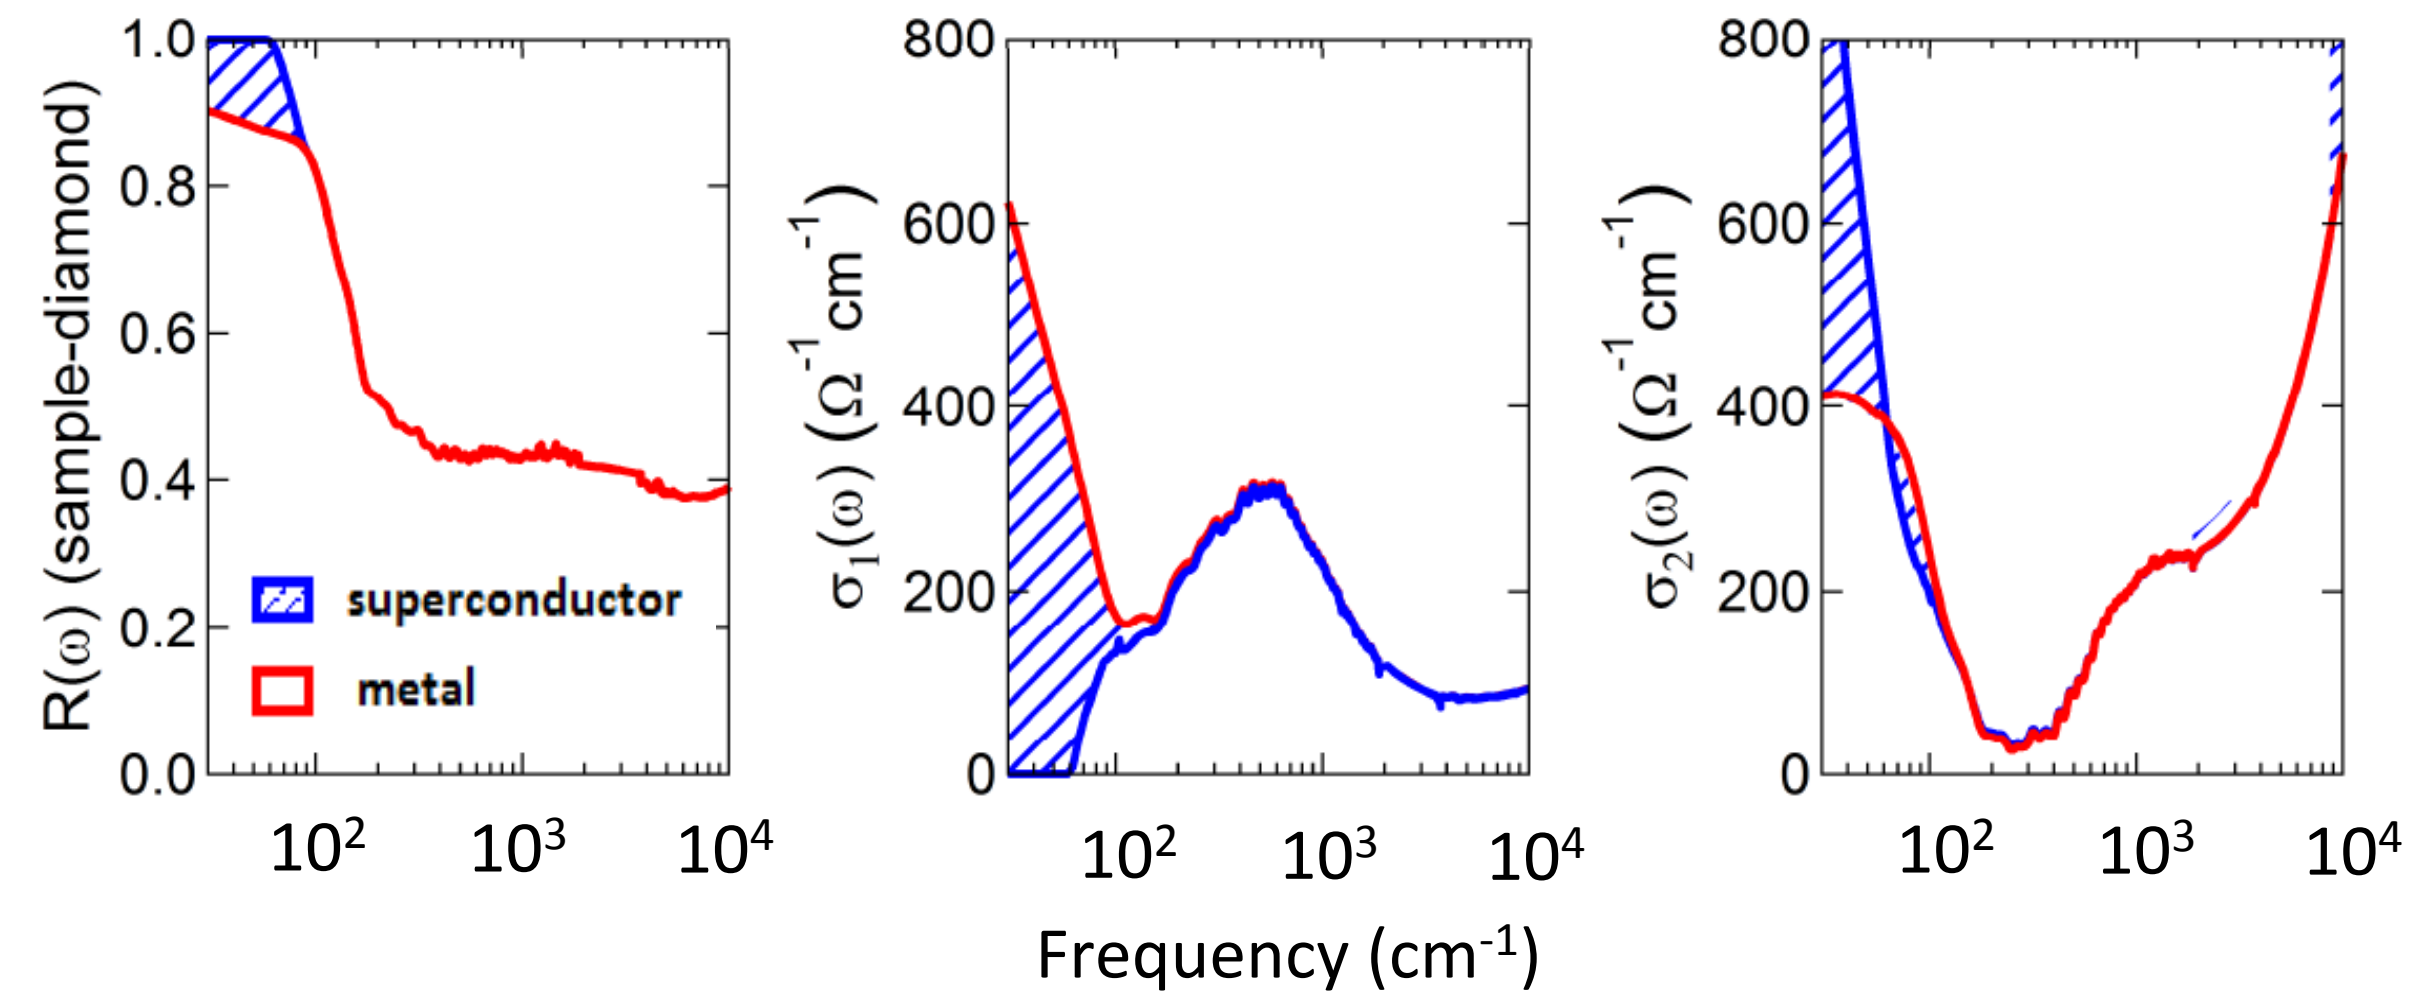

Light-Induced
 $T = 5 \cdot T_c$


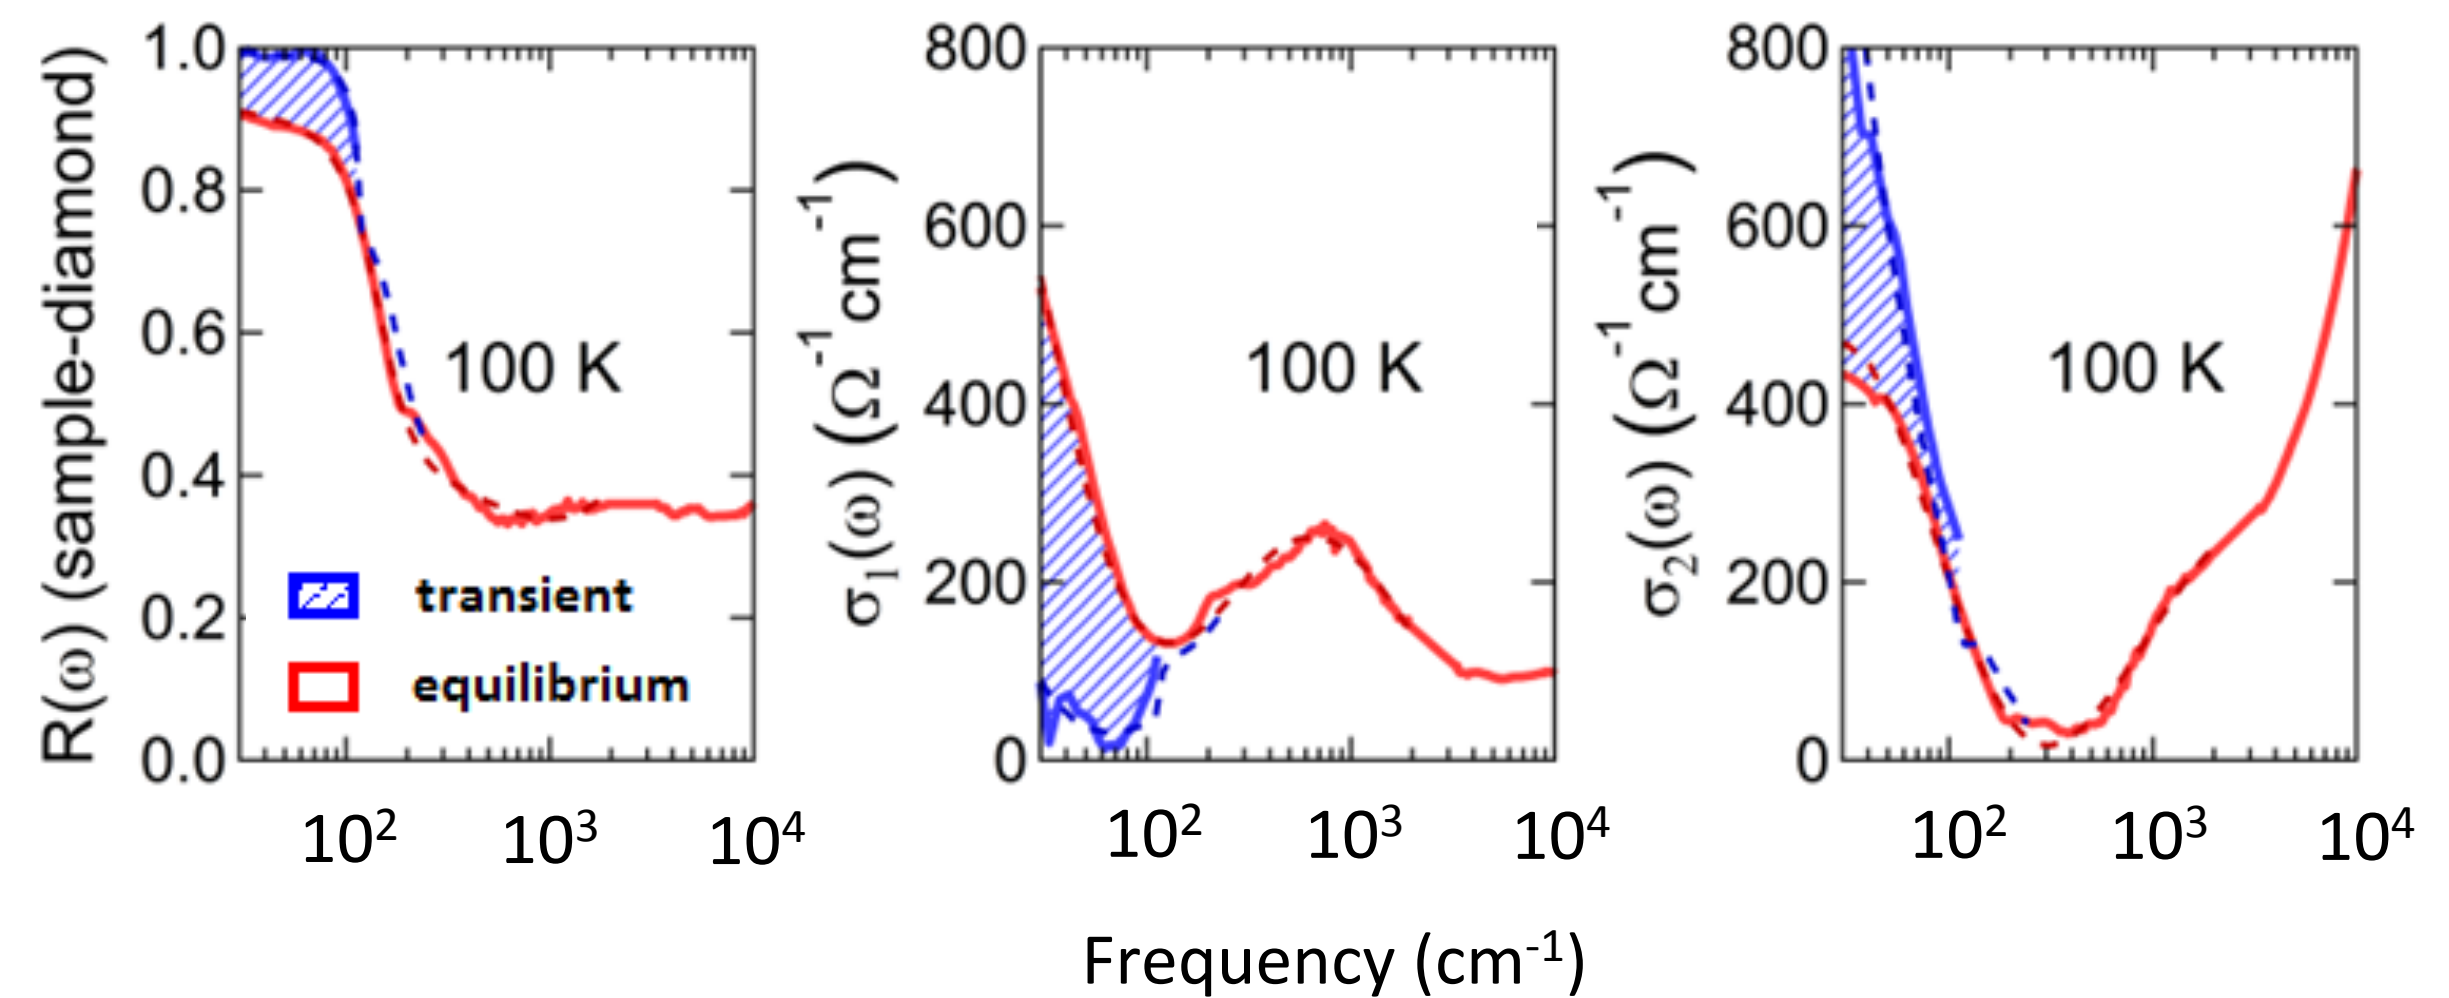


Light-induced superconductivity

M. Buzzi et al., PRX 10, 031028 (2020)

What about other materials? Can we get a handle on the microscopic mechanism?

BEDT-TTF a.k.a. ET

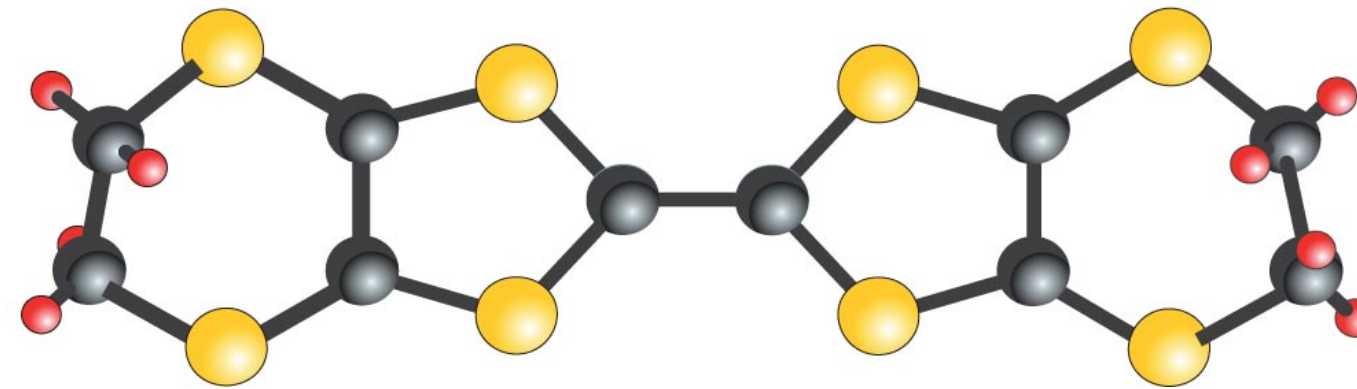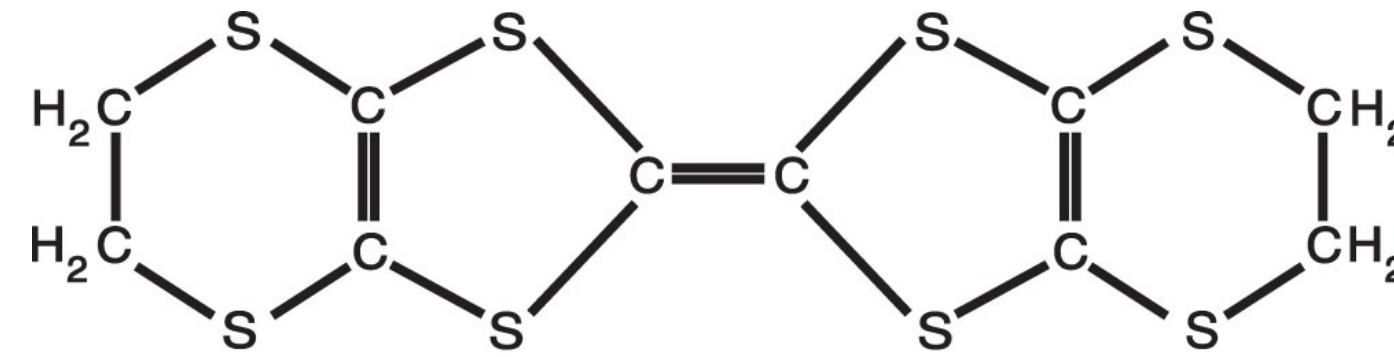


Building block of many organic charge transfer salts

Typically electron donor



Light-induced superconductivity

M. Buzzi et al., PRX 10, 031028 (2020)

Photo-molecular high-temperature superconductivity in an organic kappa salt

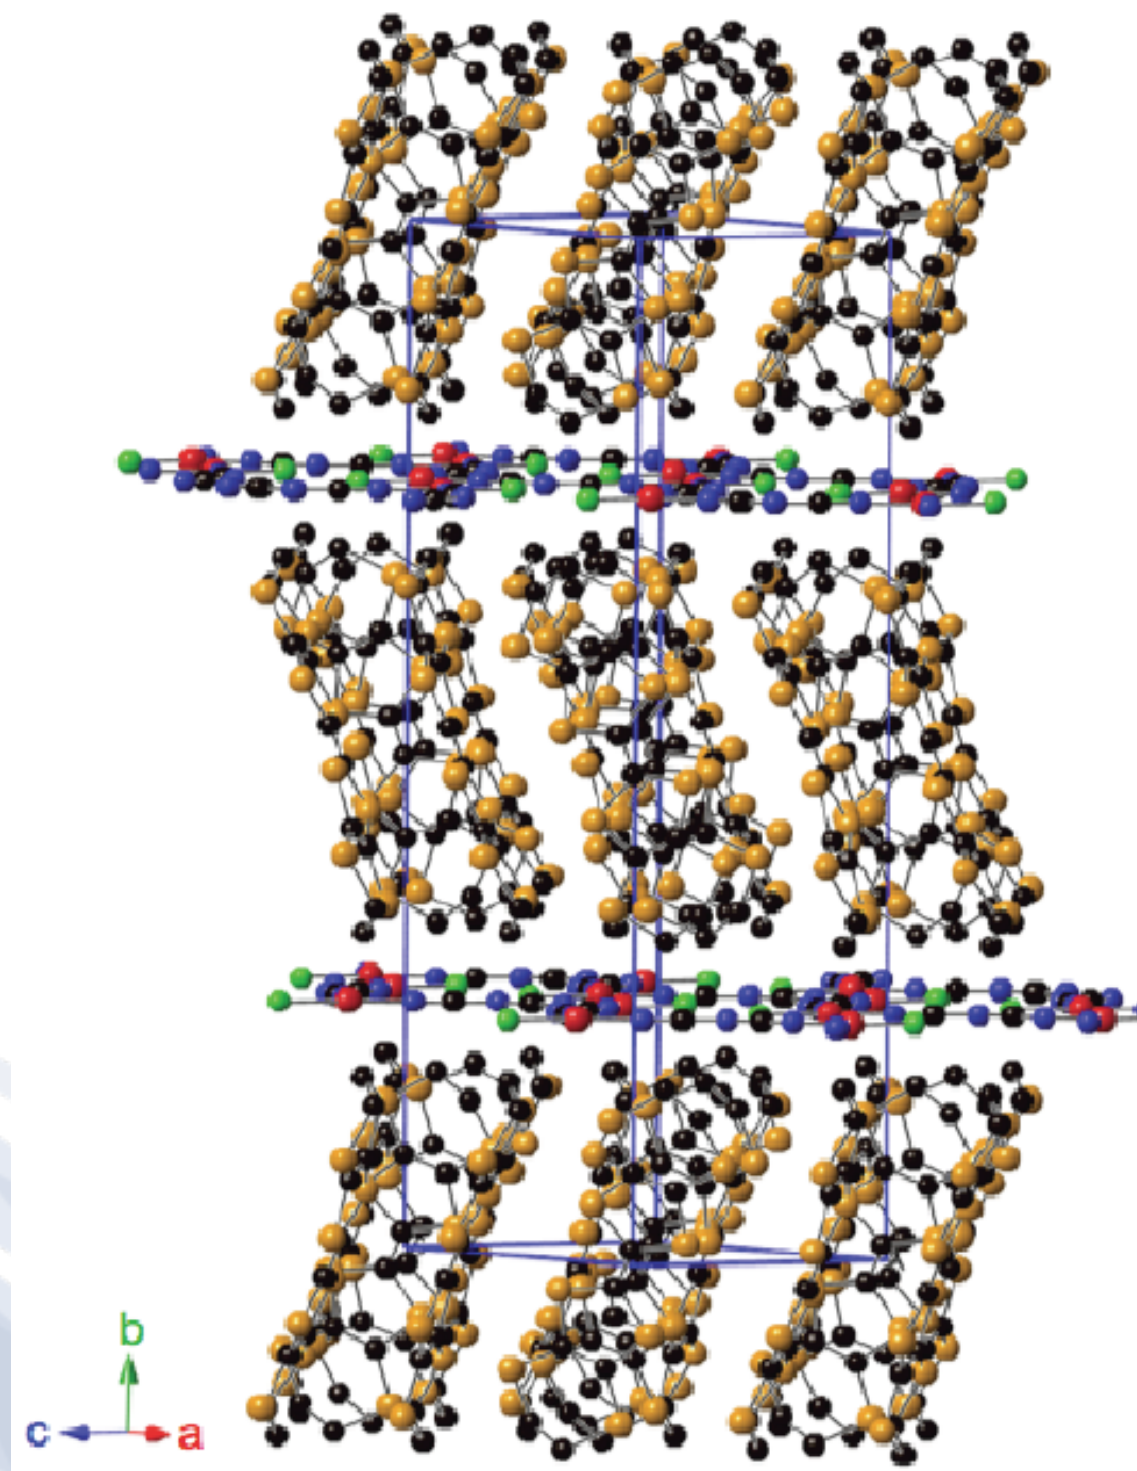

Müller et al., Crystals (2018)

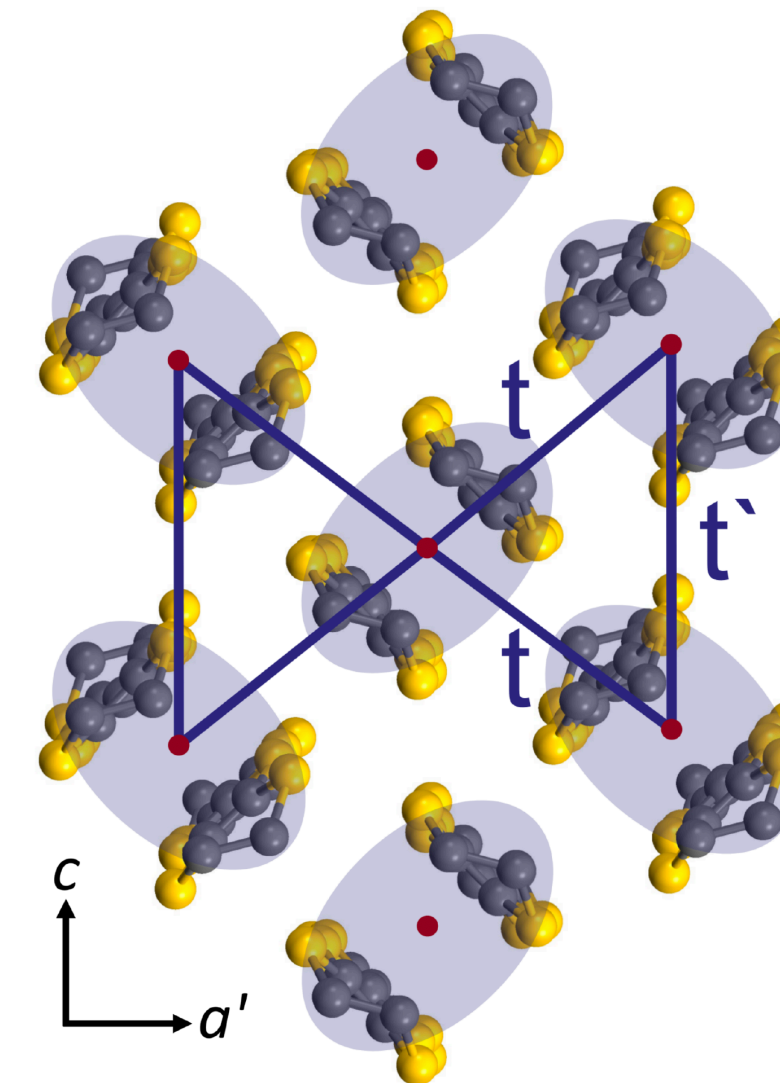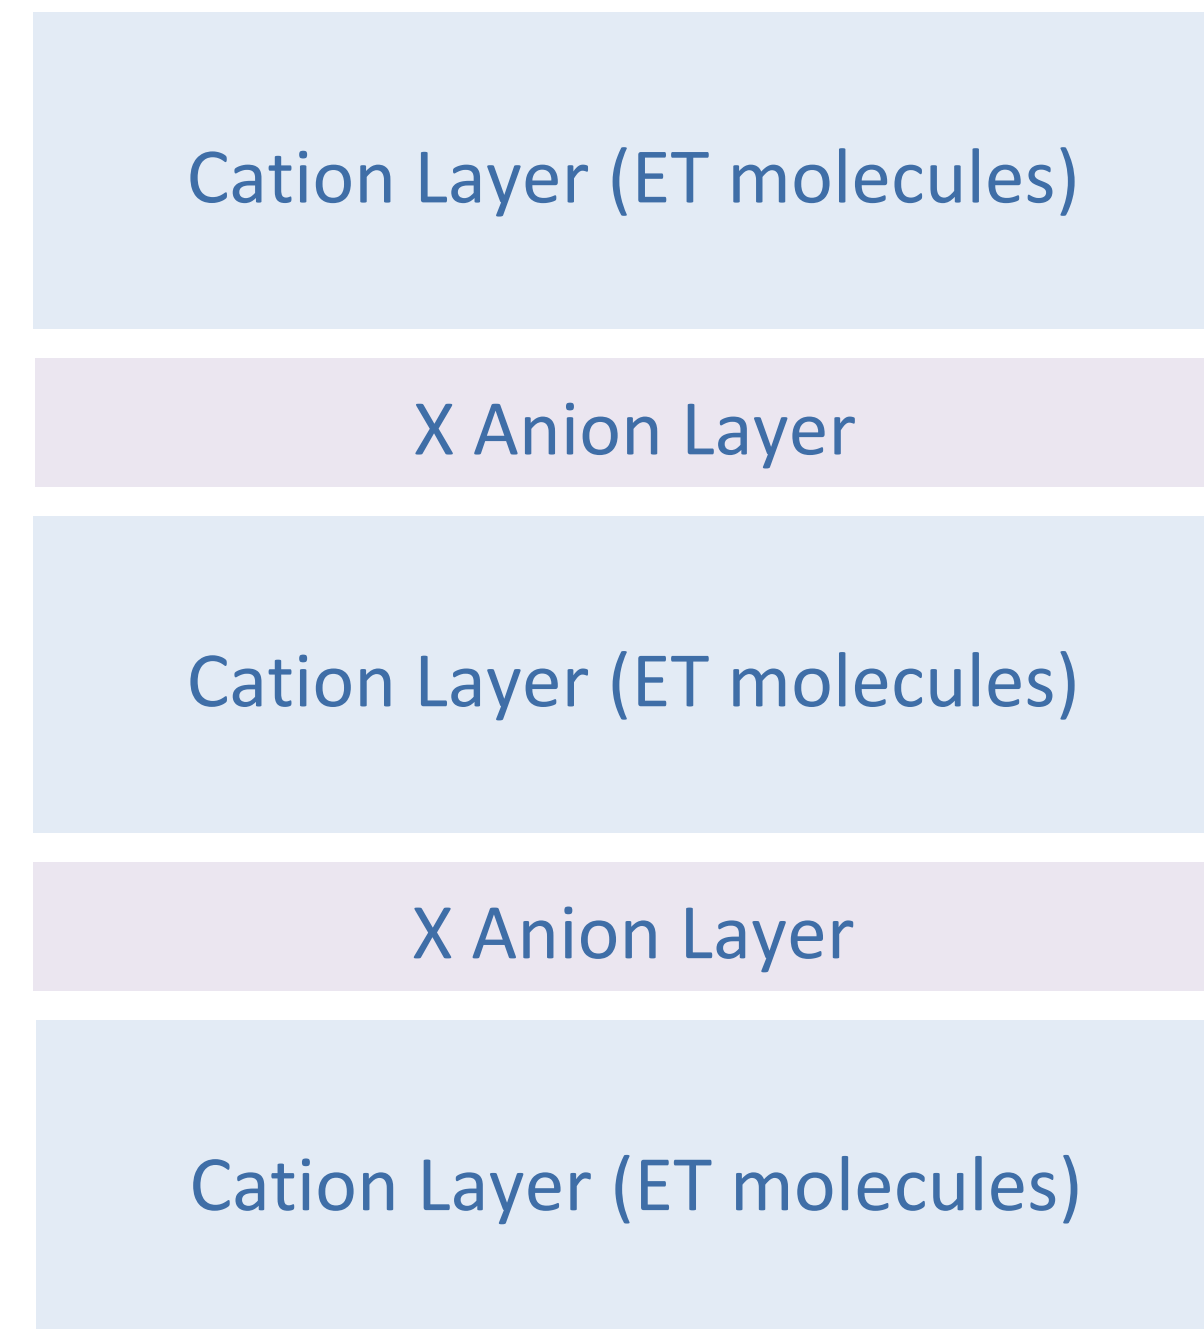

“kappa” arrangement

ET molecules paired in dimers

Half filled conduction band



Effectively a 2D U-t-t' Hubbard model on an anisotropic triangular lattice

Light-induced superconductivity

M. Buzzi et al., PRX 10, 031028 (2020)

Photo-molecular high-temperature superconductivity in an organic kappa salt

kappa-(ET)₂X phase diagram

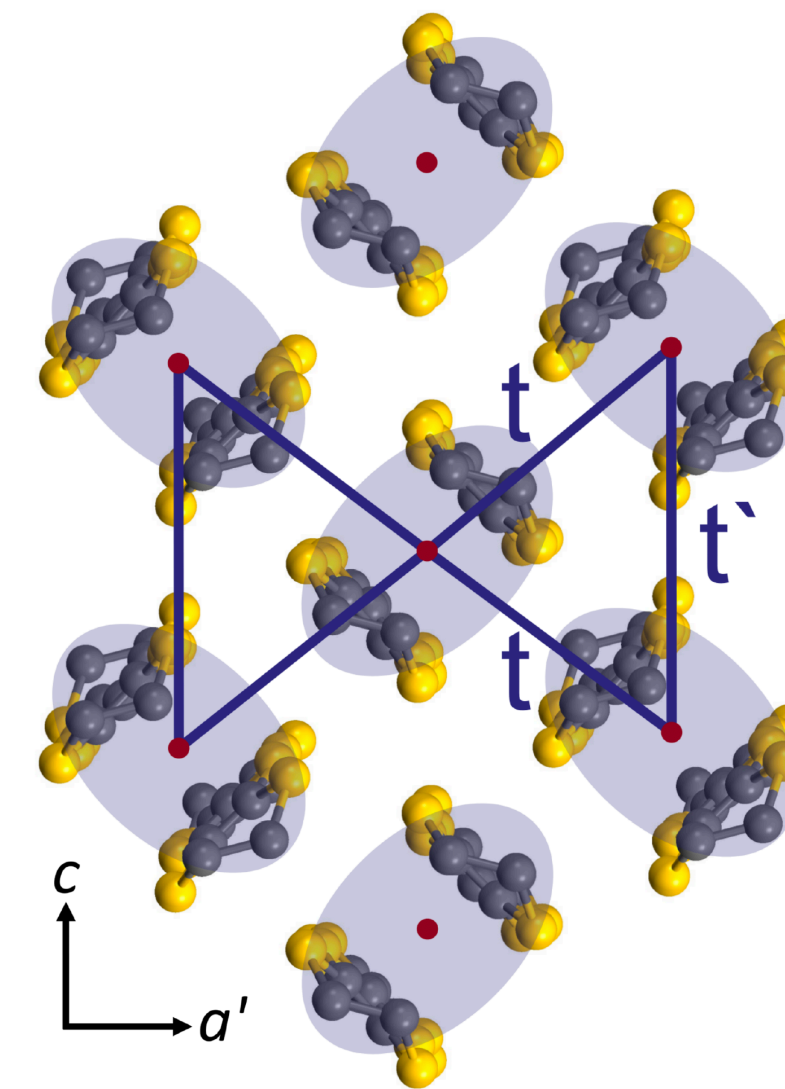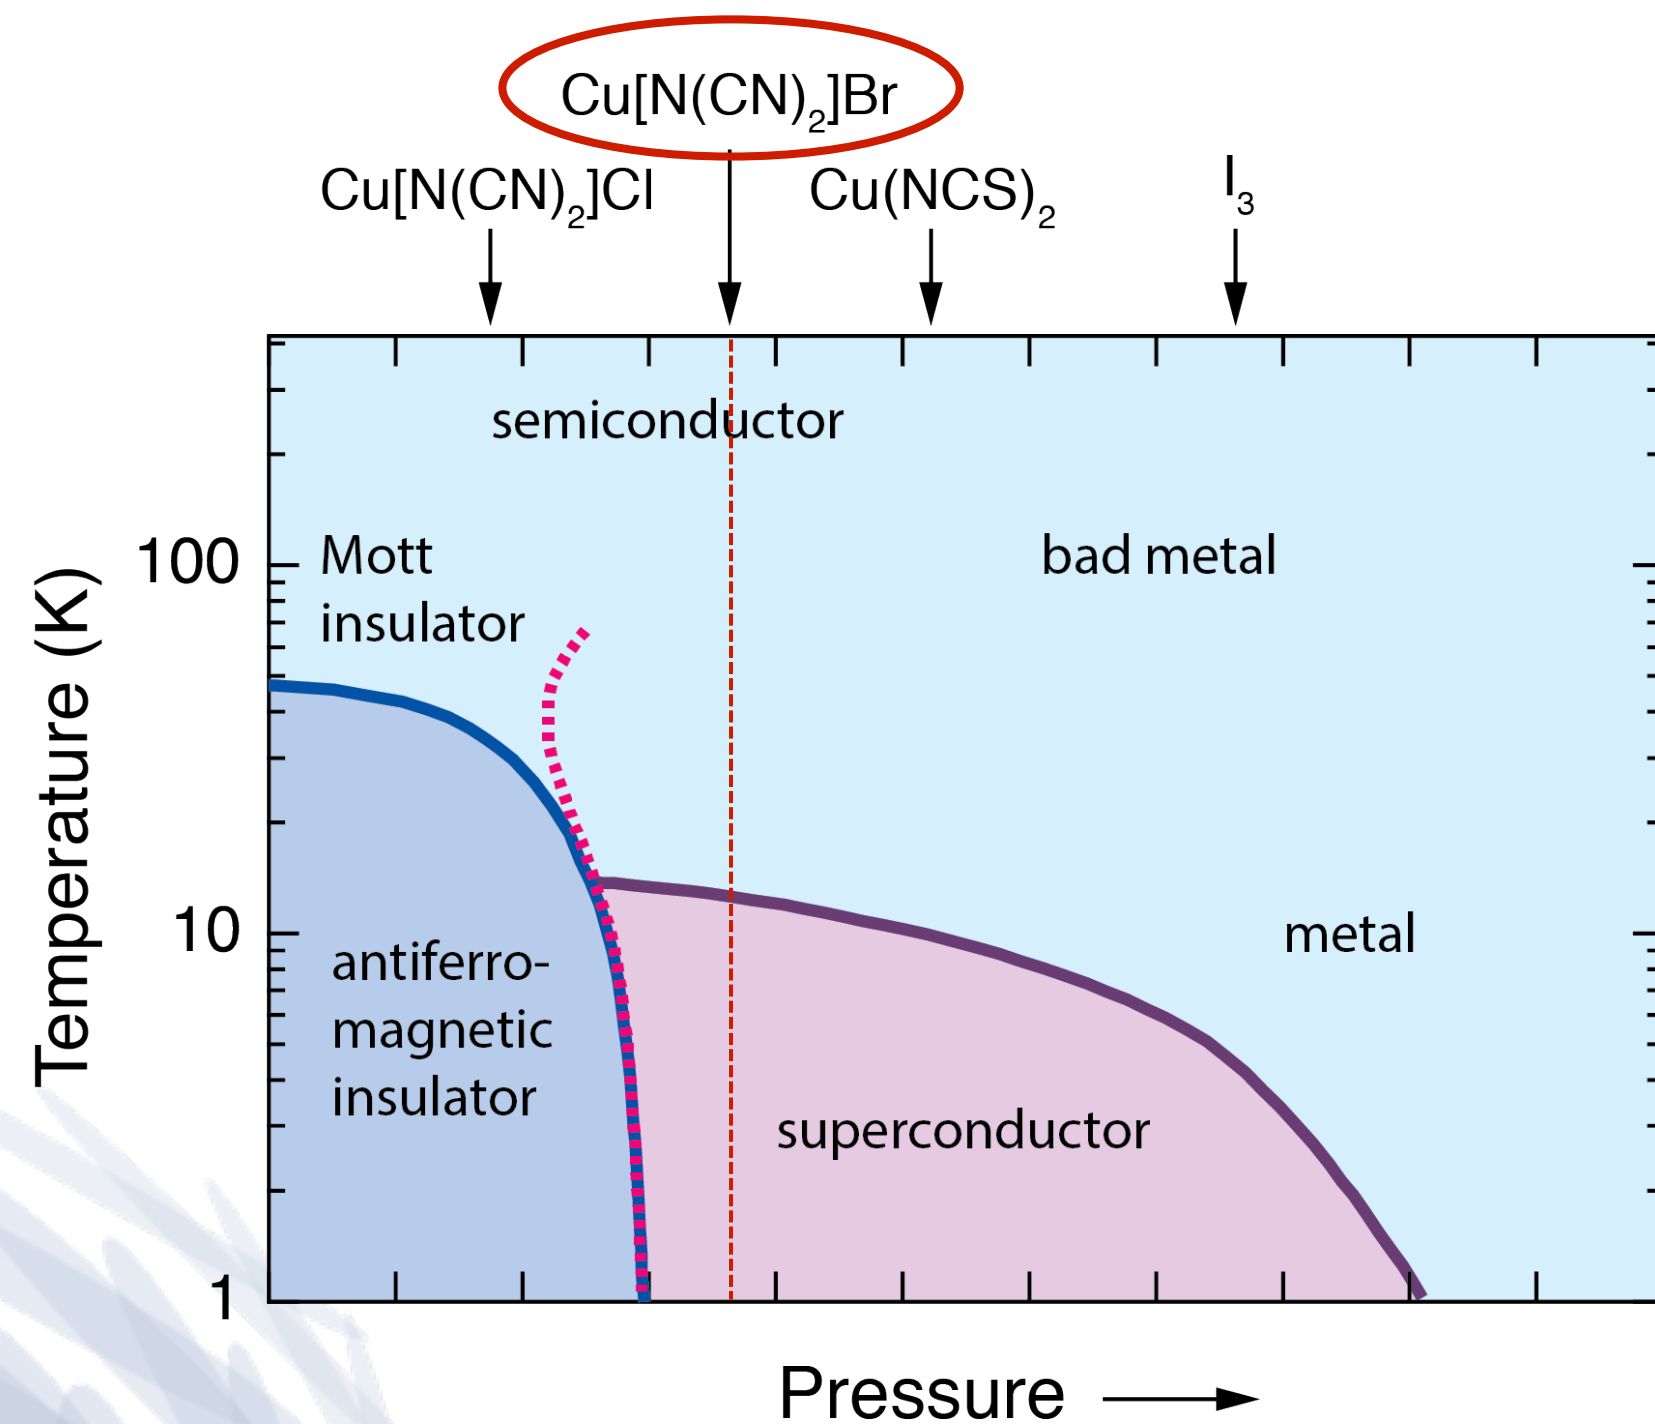

“kappa” arrangement

ET molecules paired in dimers

Half filled conduction band

D. Faltermeier *et al.*, Phys. Rev. B **76**, 165113 (2007)



Nernst effect indicating superconducting fluctuations above T_c:
M.-S. Nam *et al.*, Nature **449**, 584 (2007)

Light-induced superconductivity

M. Buzzi et al., PRX 10, 031028 (2020)

Photo-molecular high-temperature superconductivity in an organic kappa salt


Driving with a specific molecular vibration

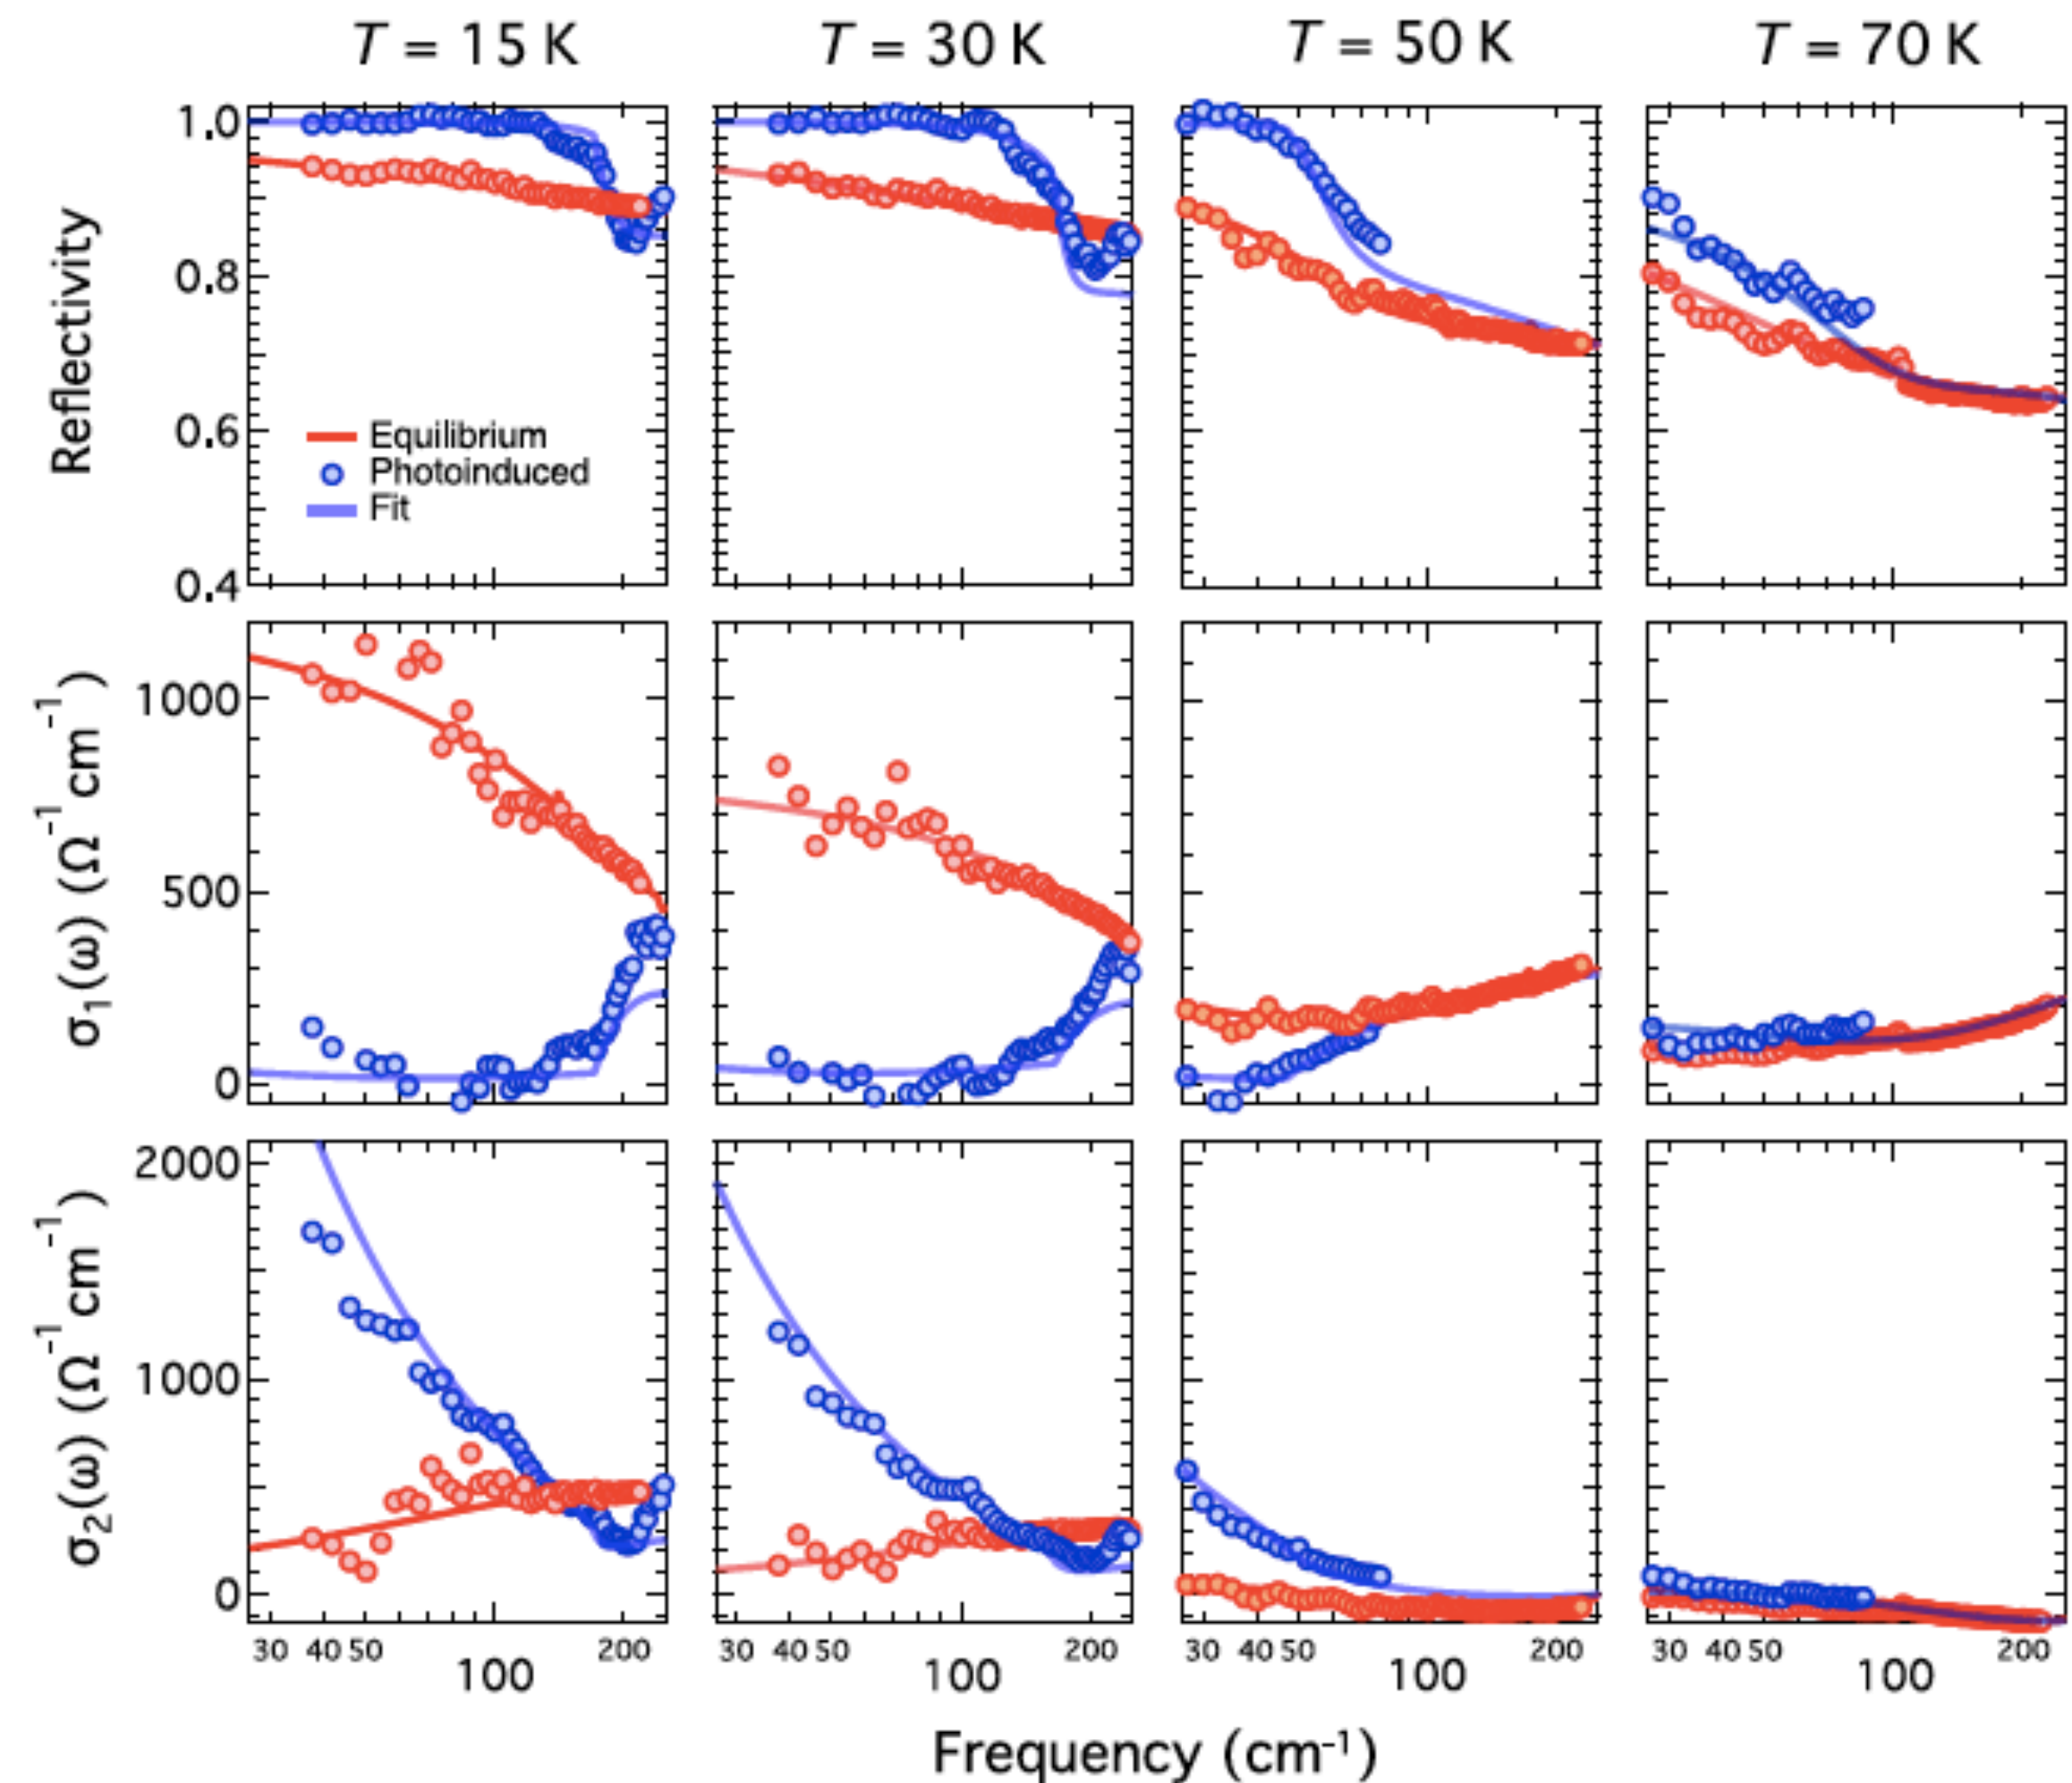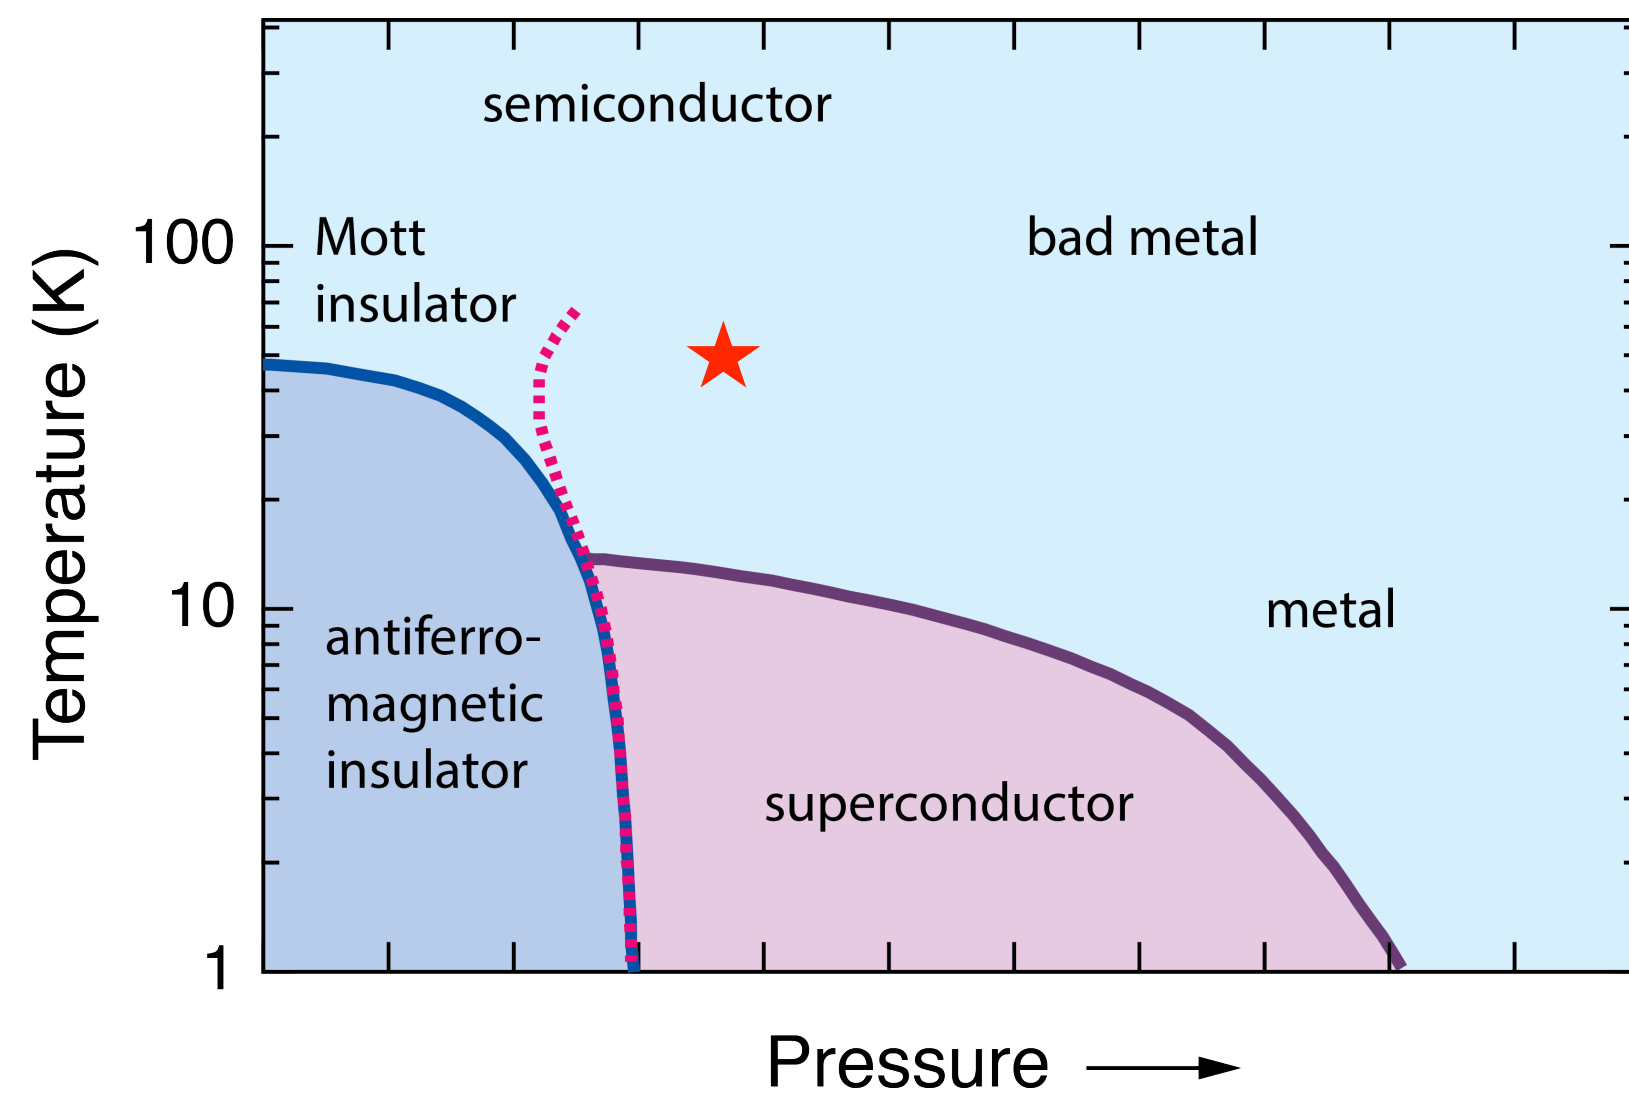



Light-induced superconductivity

M. Buzzi et al., PRX 10, 031028 (2020)

Photo-molecular high-temperature superconductivity in an organic kappa salt

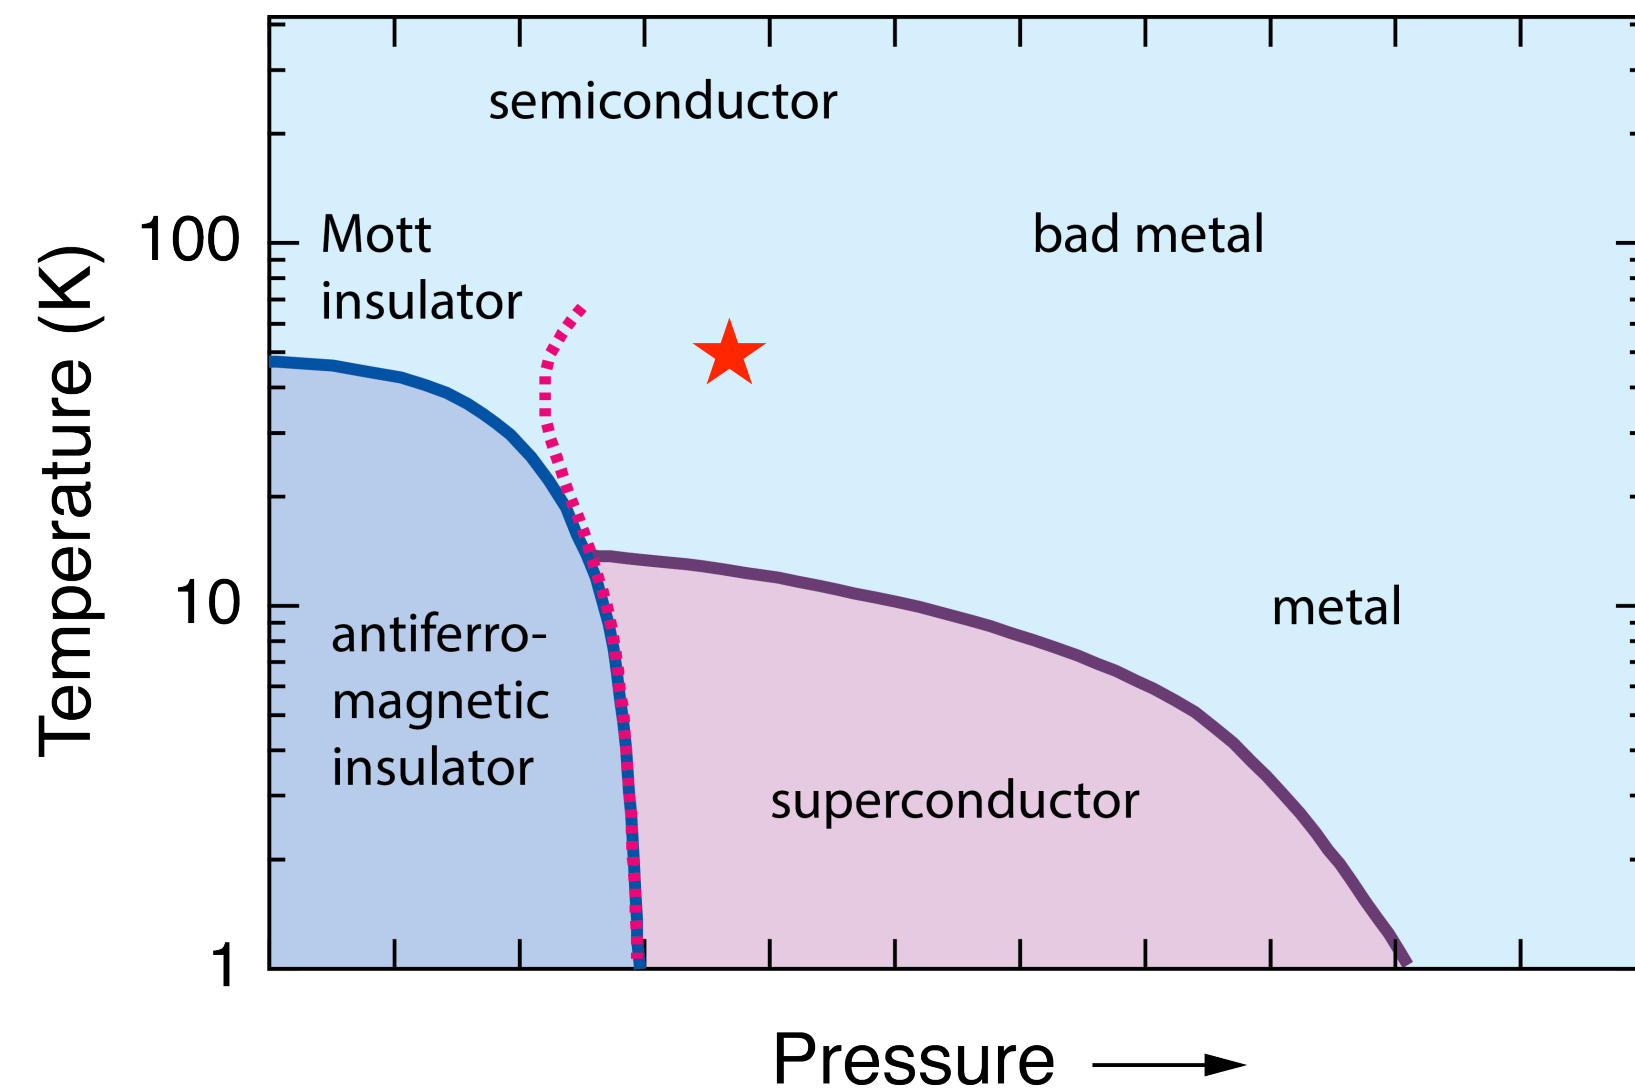

The effect persists up to 50 Kelvin!
(equilibrium $T_c = 12.5$ K)

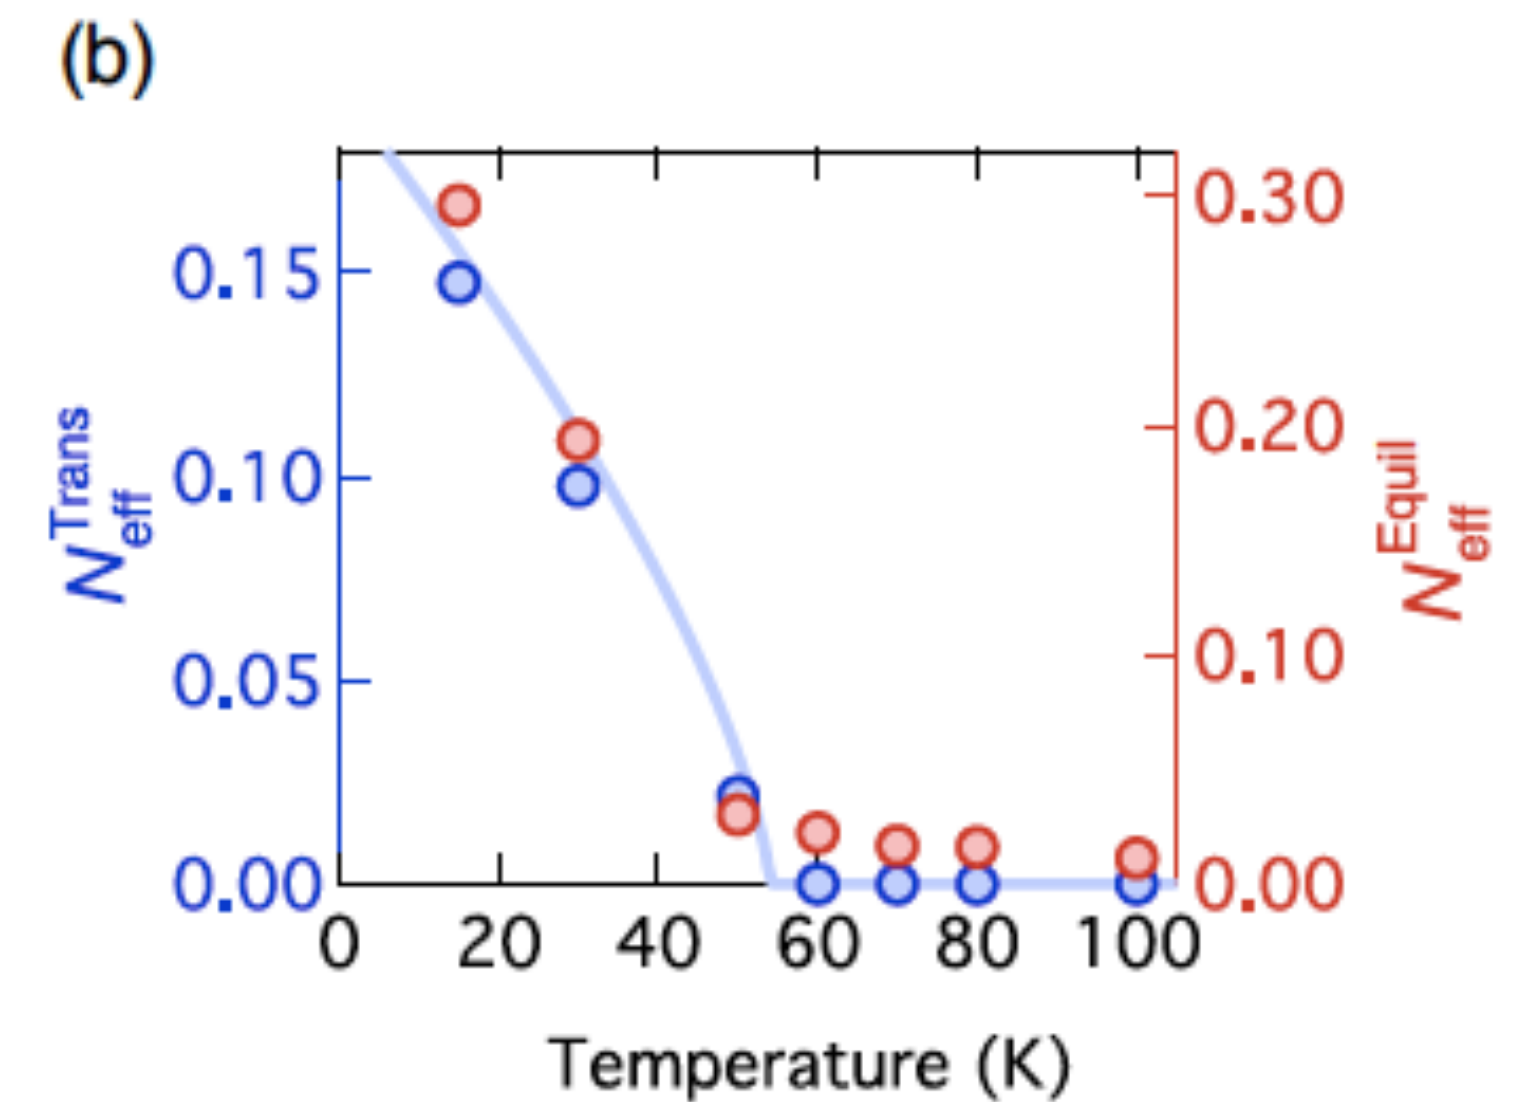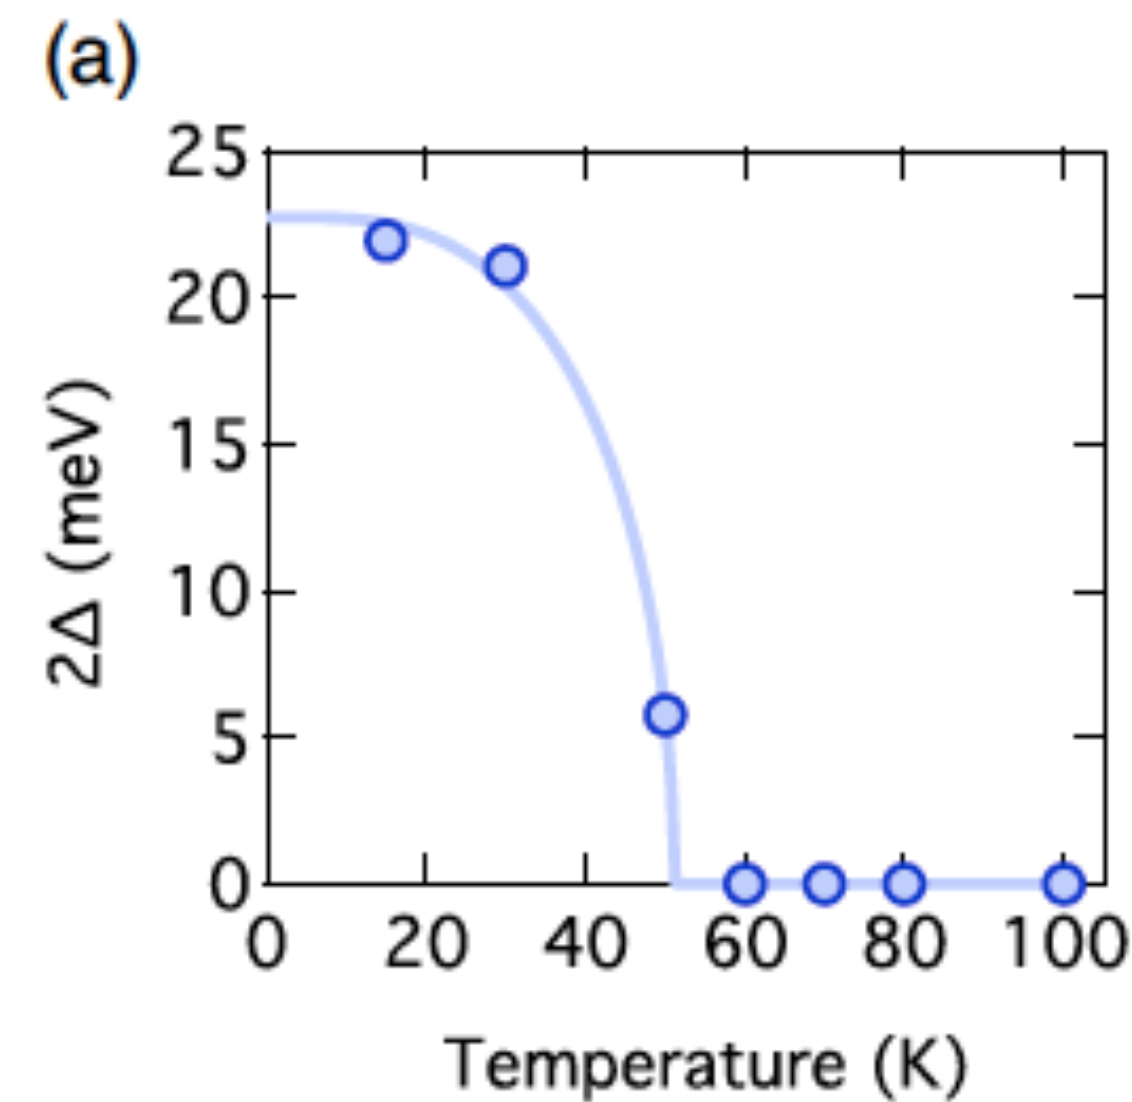


Light-induced superconductivity

M. Buzzi et al., PRX 10, 031028 (2020)

Photo-molecular high-temperature superconductivity in an organic kappa salt

It only works for specific molecular vibrations


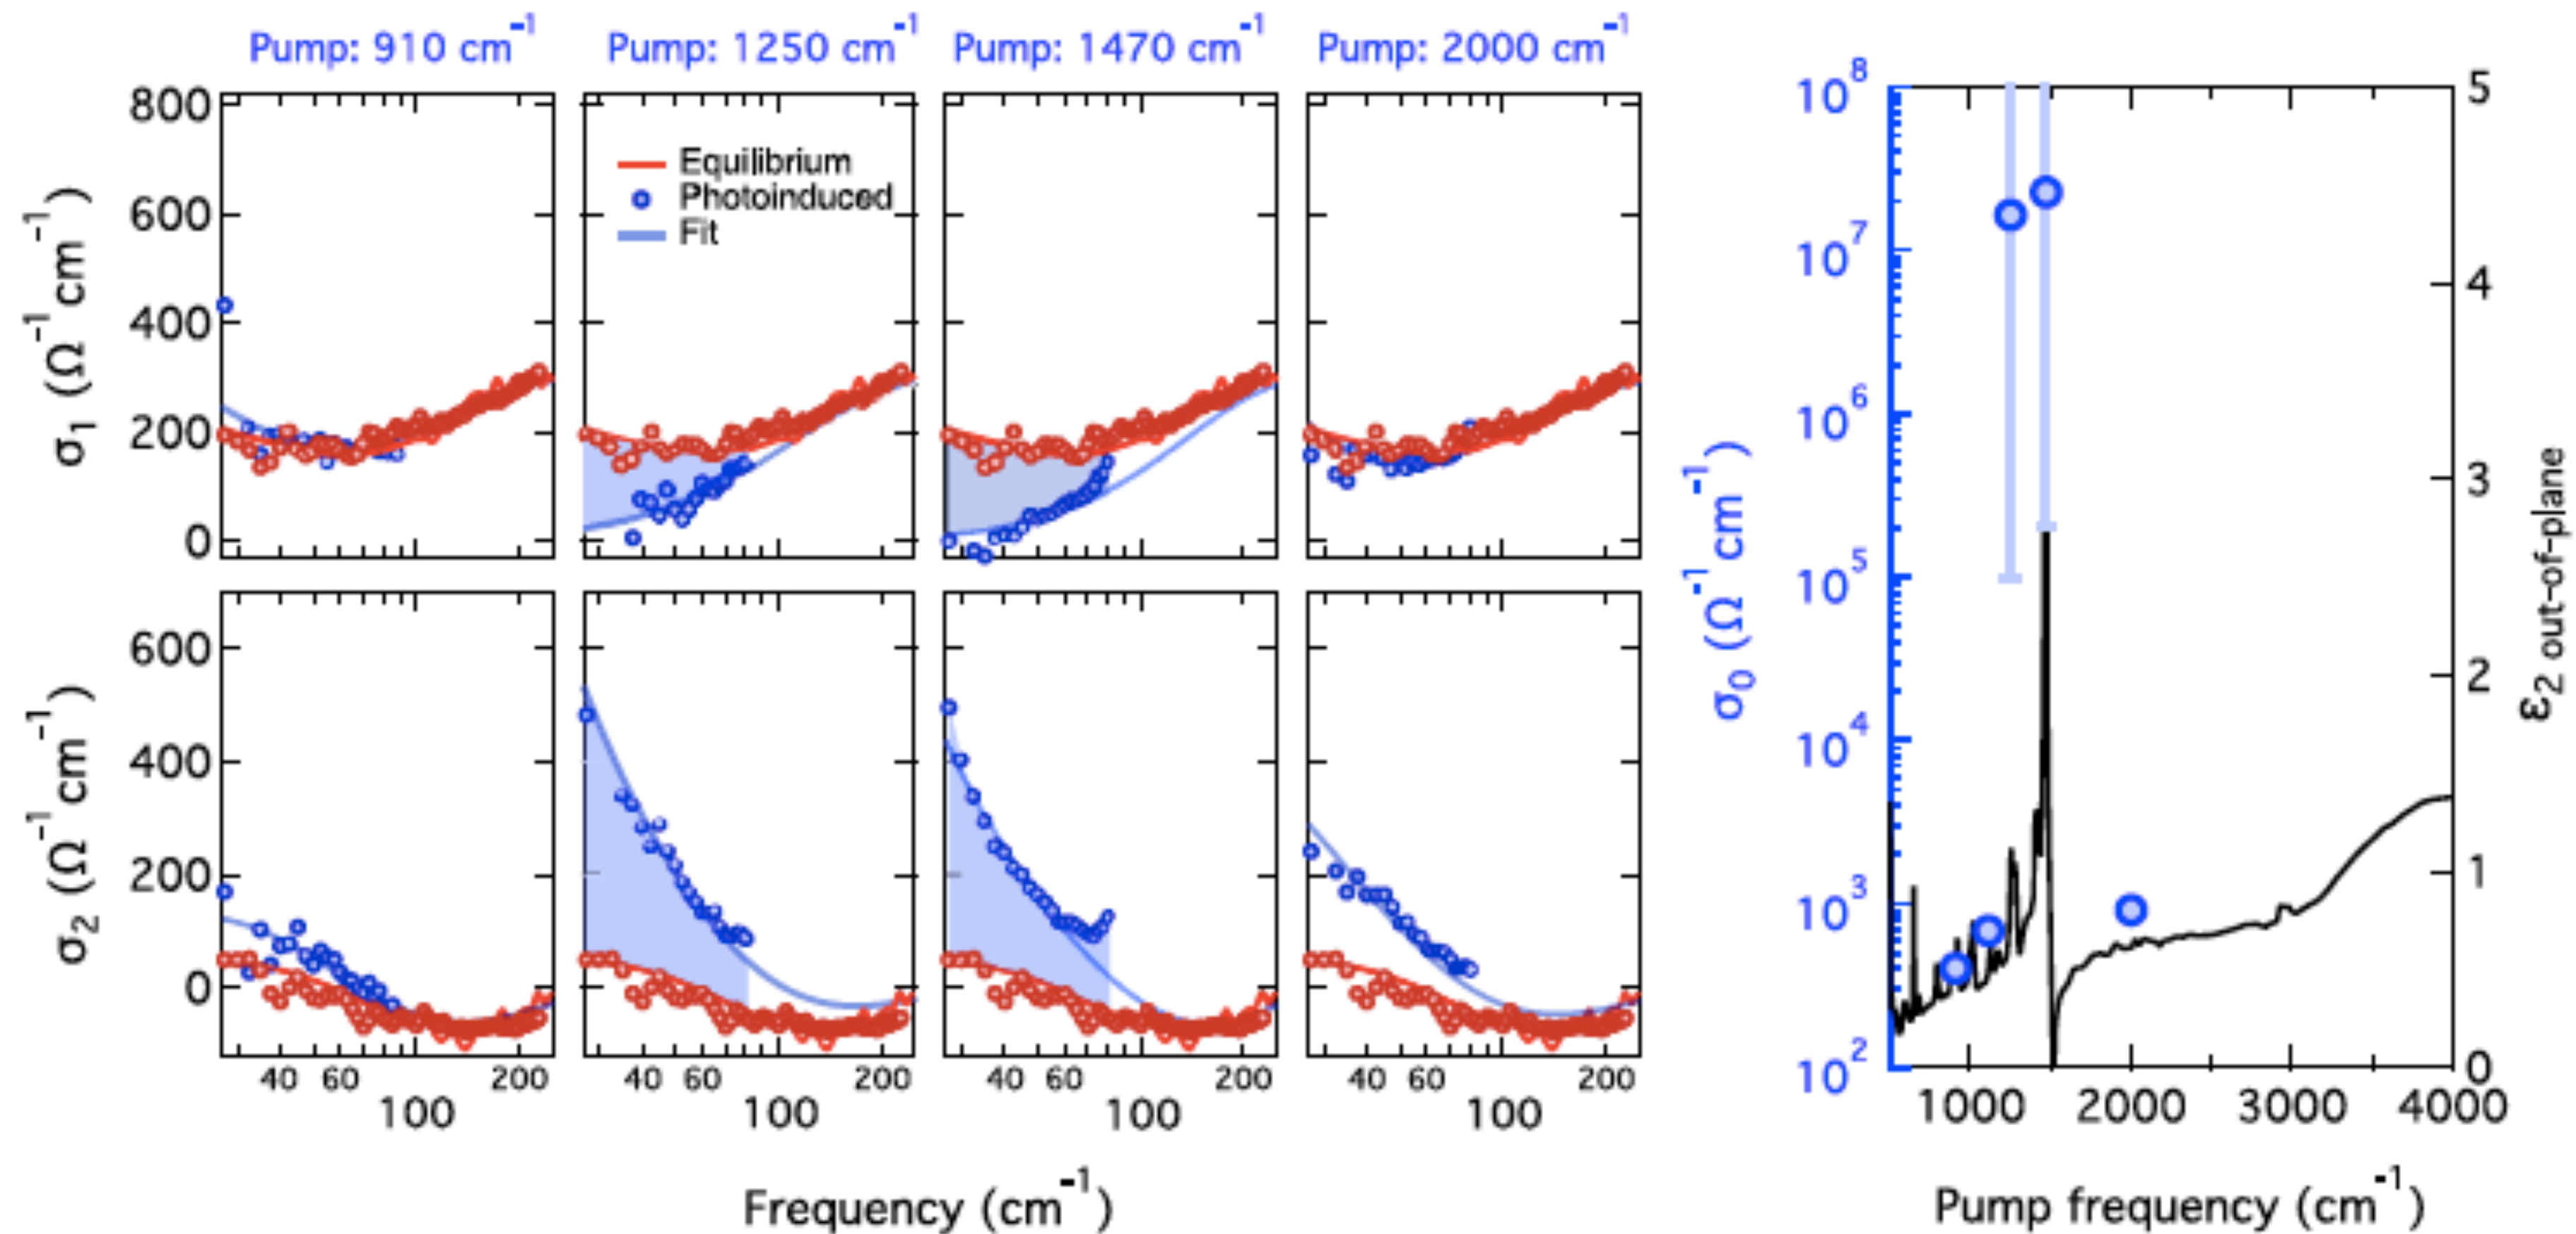


Light-induced superconductivity

M. Buzzi et al., PRX 10, 031028 (2020)

Photo-molecular high-temperature superconductivity in an organic kappa salt

What is special about these vibrations?

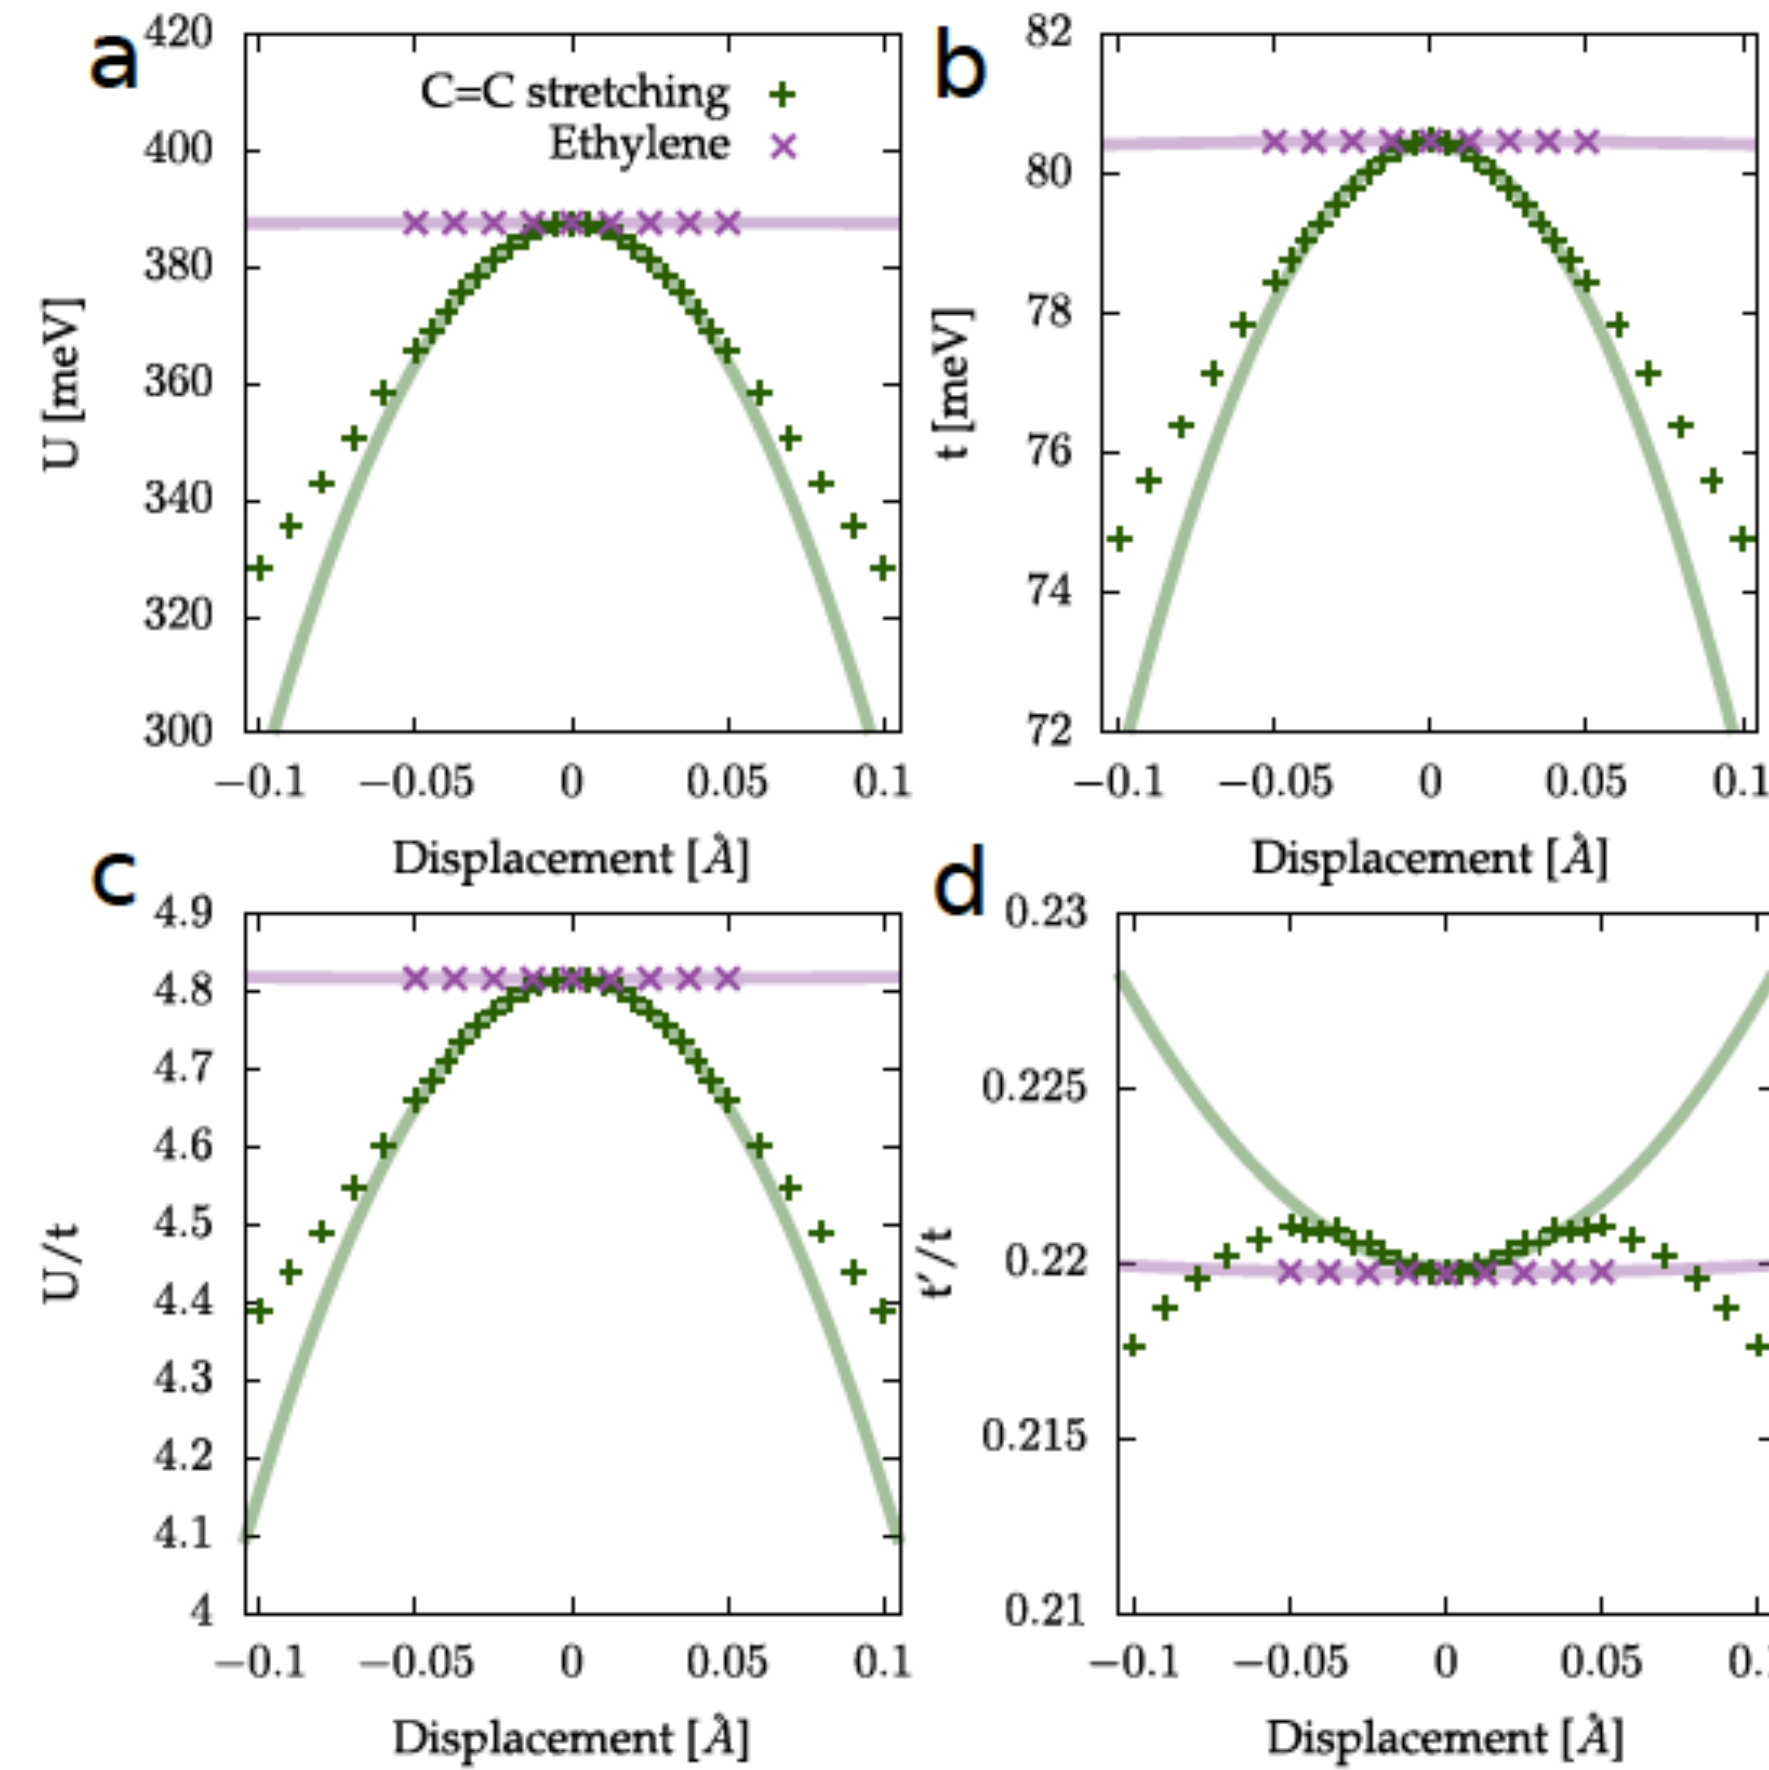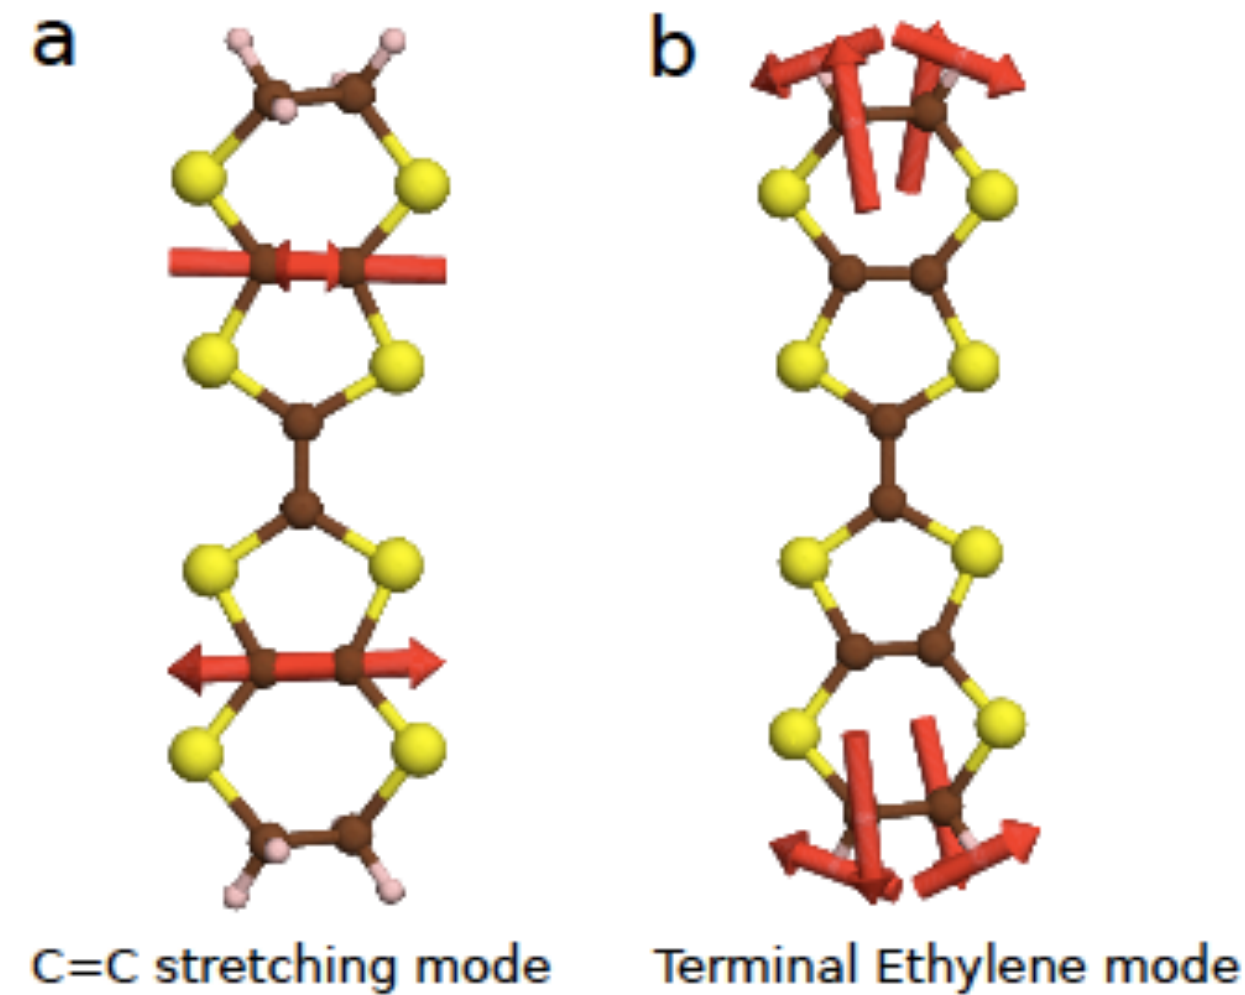

The C=C bond stretching modes change Hubbard U!

$$H = \sum_{\langle ij \rangle, \sigma} t(c_{i\sigma}^\dagger c_{j\sigma} + H.c.) + \sum_{[ij], \sigma} t'(c_{i\sigma}^\dagger c_{j\sigma} + H.c.) + U \sum_i (n_{i\uparrow} - \frac{1}{2})(n_{i\downarrow} - \frac{1}{2})$$


Light-induced superconductivity

M. Buzzi et al., PRX 10, 031028 (2020)


Photo-molecular high-temperature superconductivity in an organic kappa salt

What is special about these vibrations?

(a) C=C stretching mode (1470 cm^{-1})


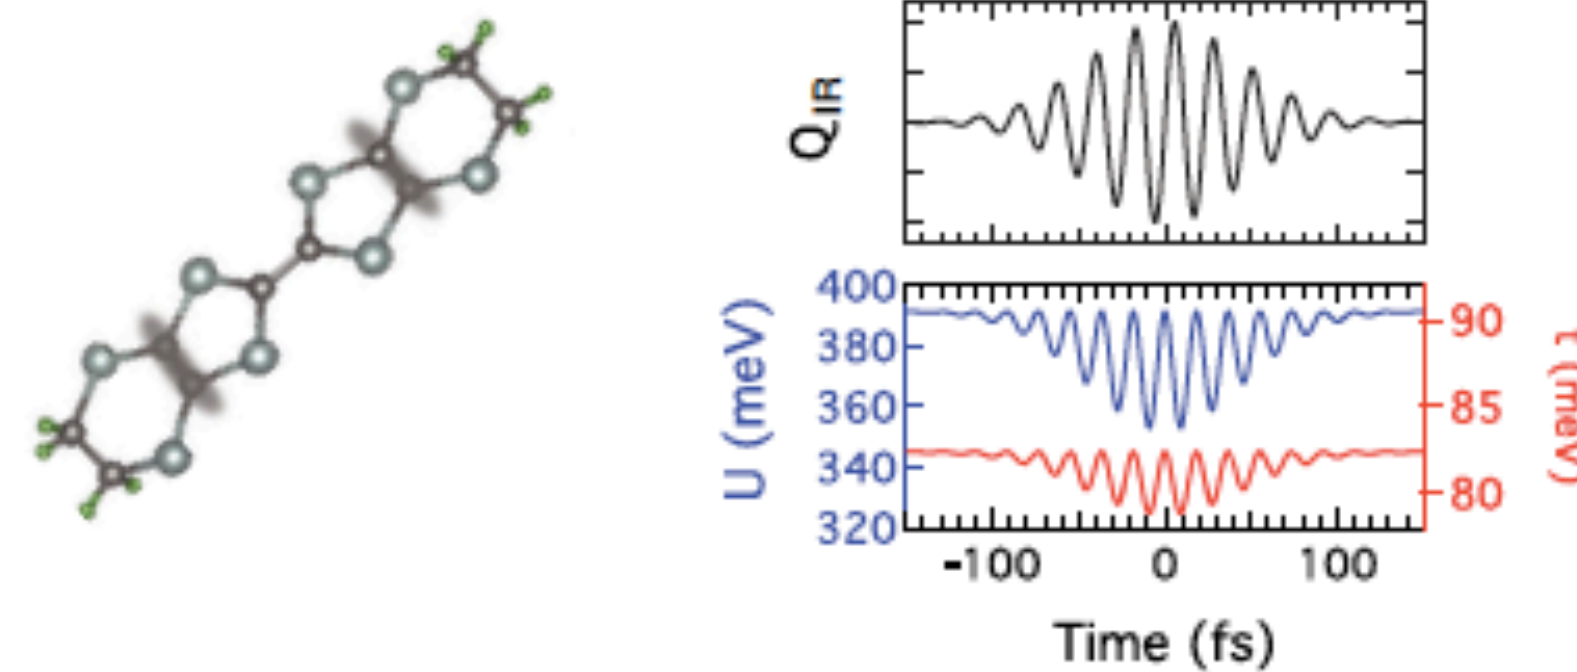


tensor net calculations for dynamically driven U-t-t' Hubbard diamond chain

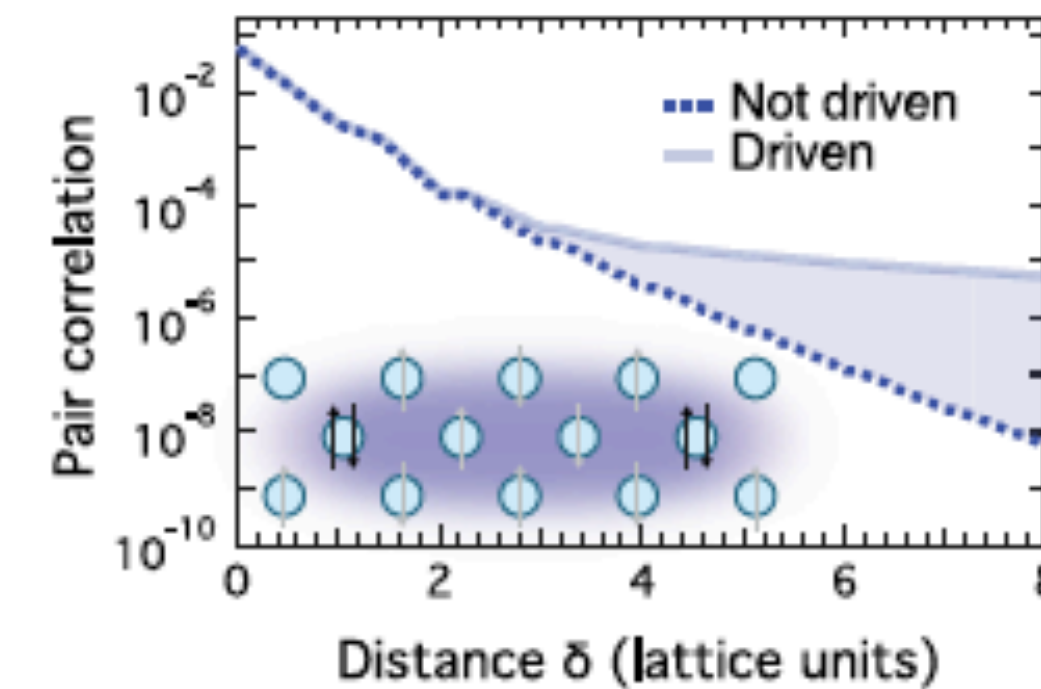

We find an enhancement of long-range pair correlations in a Hubbard system driven via $U(t)$

(b) Terminal ethylene mode (920 cm^{-1})

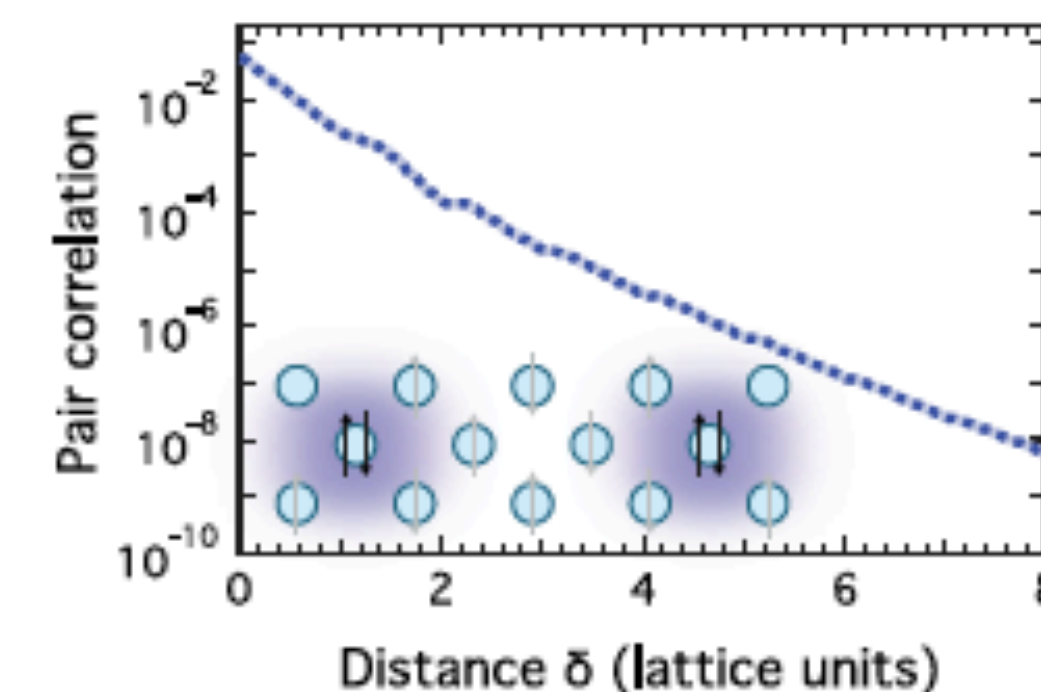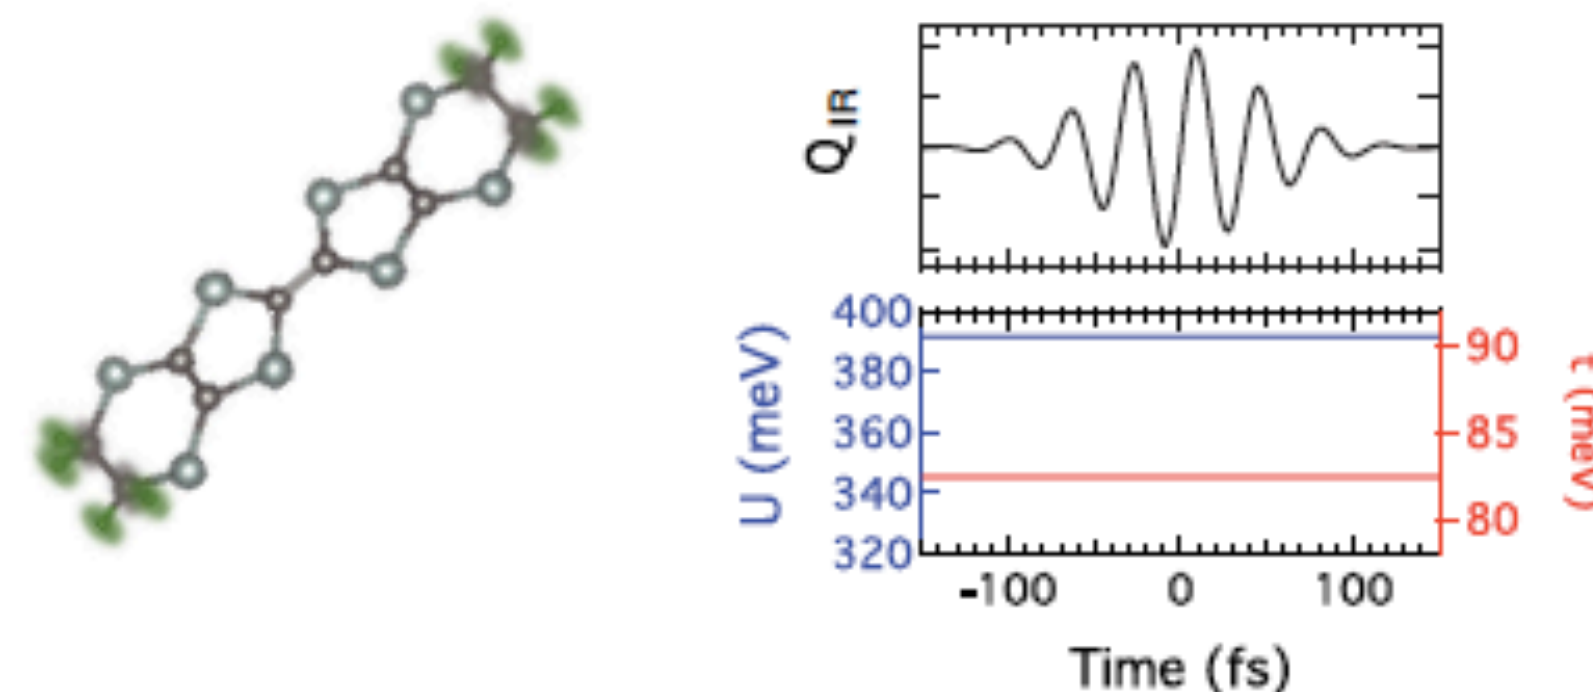


Theory follow-up:
J. Tindall et al., PRL 125, 137001 (2020)

Light-induced superconductivity

M. Buzzi et al., PRX 10, 031028 (2020)

Photo-molecular high-temperature superconductivity in an organic kappa salt

Theory follow-up:
J. Tindall et al., PRL
125, 137001 (2020)

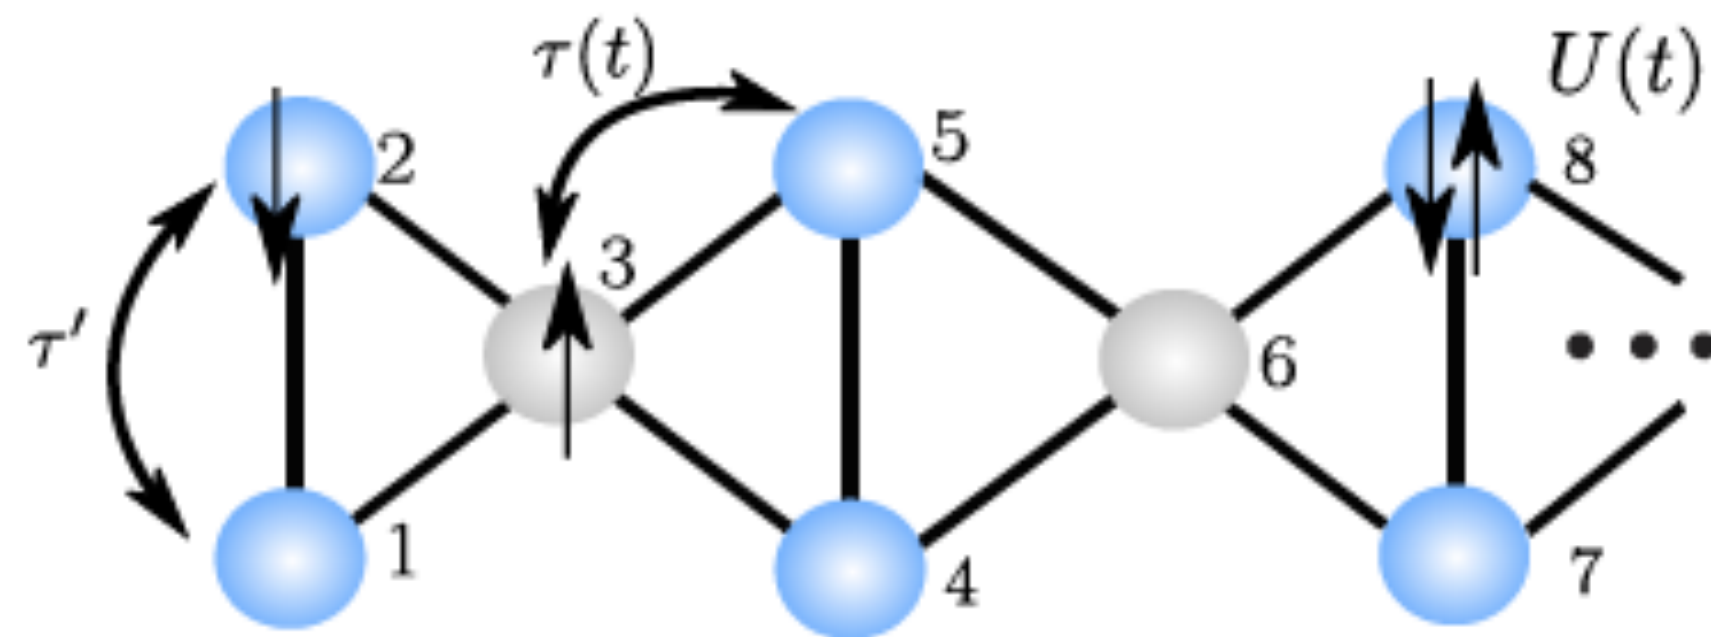

$$H(t) = -\tau(t) \sum_{ij \in \langle \text{n.n.} \rangle, \sigma} (c_{\sigma,i}^\dagger c_{\sigma,j} + \text{h.c.}) - \tau' \sum_{ij \in \langle \text{vert} \rangle, \sigma} (c_{\sigma,i}^\dagger c_{\sigma,j} + \text{h.c.}) + U(t) \sum_i n_{i,\uparrow} n_{i,\downarrow},$$

Approximate eta SU(2) symmetry (exact for $\tau'=0$, bipartite lattice):

$$[H(t), \eta^z] \equiv 0, \quad [H(t), \eta^+ \eta^-] \propto \tau', \quad (3)$$

where

$$\eta^+ = \sum_{i=1}^L f(i) c_{i,\uparrow}^\dagger c_{i,\downarrow}^\dagger, \quad \eta^z = \sum_i (n_{\uparrow,i} + n_{\downarrow,i} - 1), \quad (4)$$


put reference to Yang & Zhang, SO4 paper

Light-induced superconductivity


M. Buzzi et al., PRX 10, 031028 (2020)

Photo-molecular high-temperature superconductivity in an organic kappa salt

Theory follow-up:
J. Tindall et al., PRL
125, 137001 (2020)

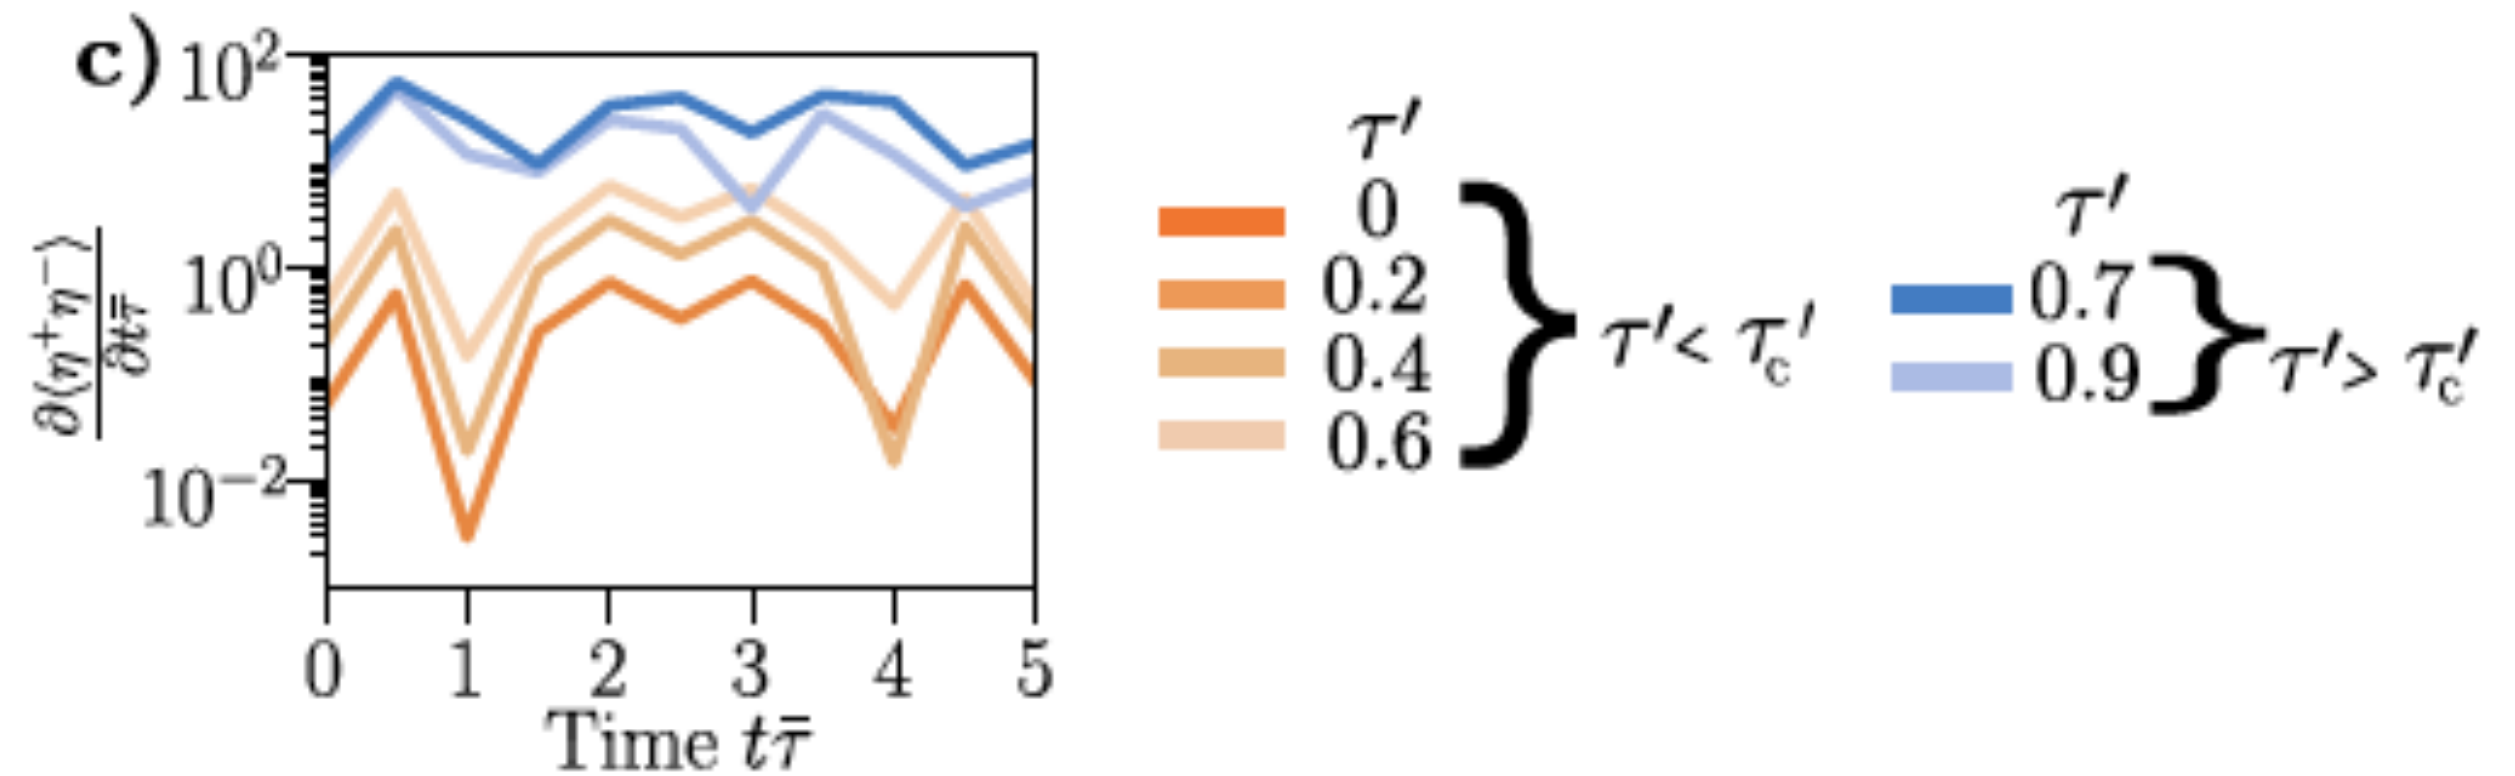

Rate of change of total $\langle \eta^+ \eta^- \rangle$ tends to zero for τ' to zero

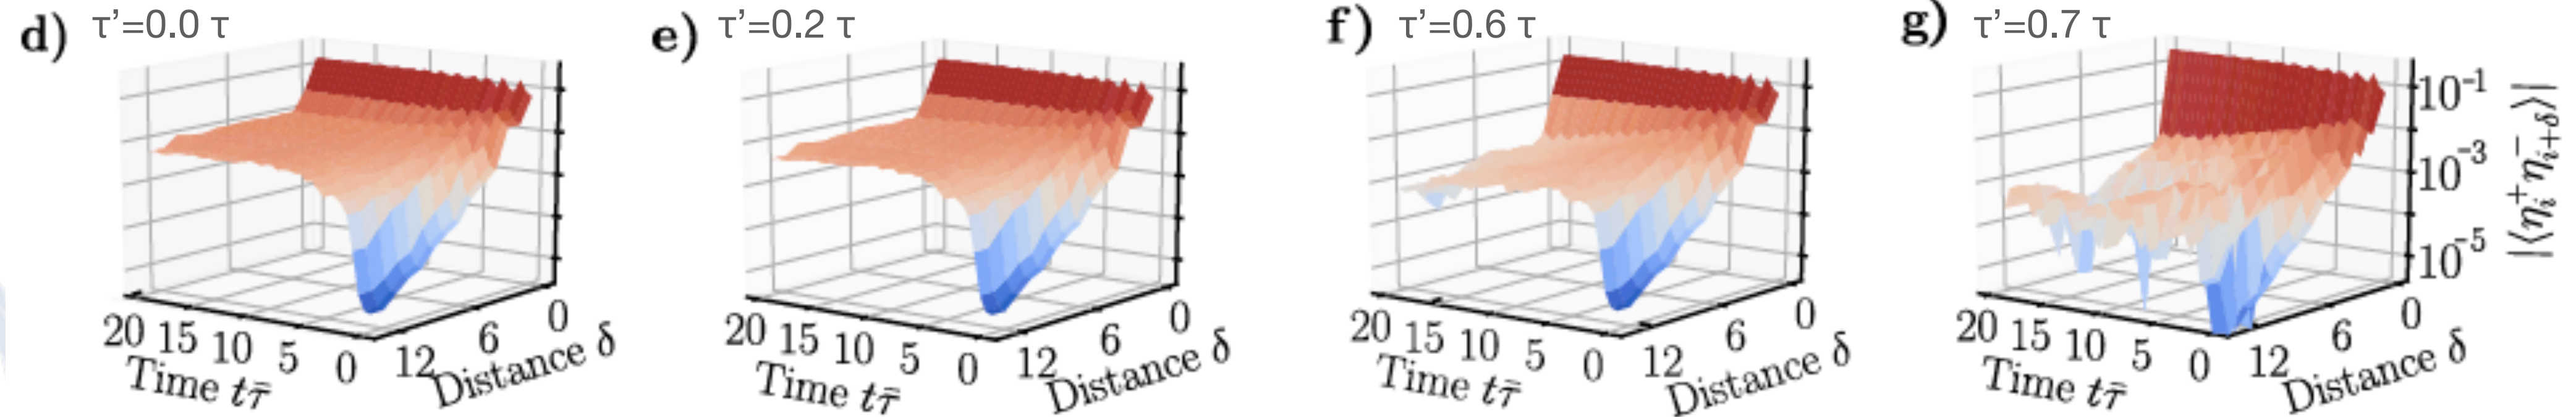


Enhancement of long-range pairing persists
up to a critical value of $\tau'=0.7\tau$

„heating-induced order“: driving heats the system
maximizing its entropy subject to symmetry constraints

Light-induced superconductivity

What is the big picture?

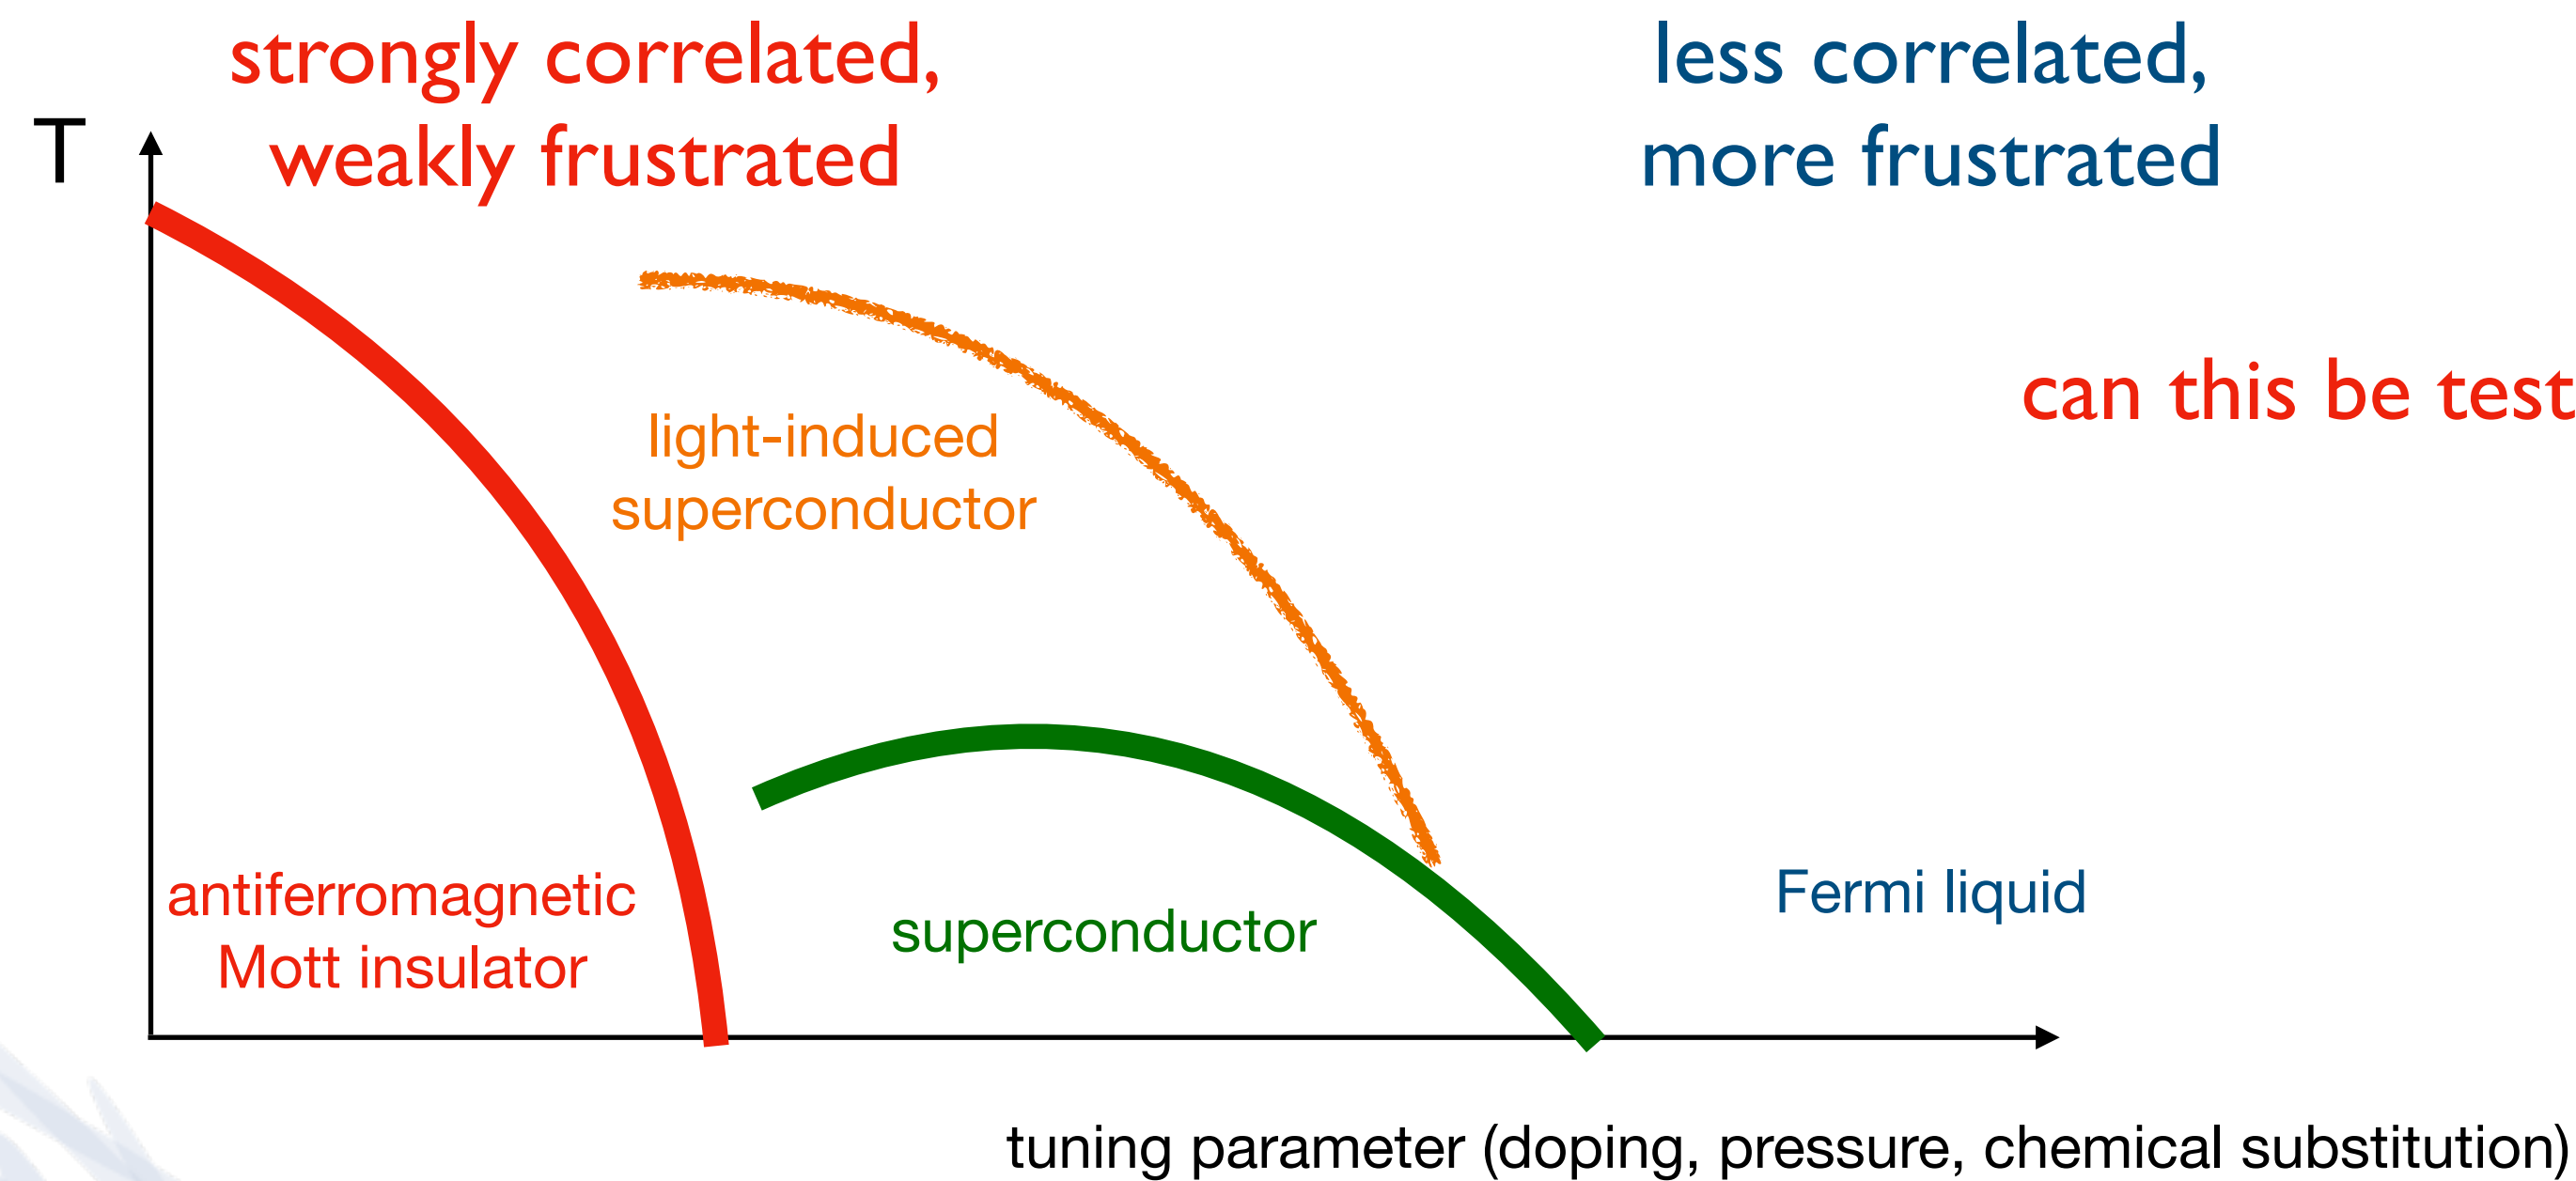

can this be tested for a 2D Hubbard model with ultracold fermions?

what are ideal conditions for light-induced SC?

- superconducting instability at low T
- temperature typically 3-5 times equilibrium T_c
- intermediate to strong correlations - fluctuation regime above T_c
- driving approximately preserves a symmetry related to SC

Acknowledgments



MPSD Hamburg

Nicolas Tancogne-Dejean, Michele Buzzi, Daniele Nicoletti, Andrea Cavalleri



Oxford University

Joey Tindall, Frank Schlawin, Dieter Jaksch

Thank you for your attention!

